



# **Characterization of Corrosion on Outdoor-Exposed Aluminum Metal-Matrix Composites as a Function of Reinforcement Specie and Volume Fraction**

**by Ralph P. I. Adler, Daniel J. Snoha, George Hawthorn,  
and Lloyd H. Hihara**

**ARL-TR-4372**

**February 2008**

## **NOTICES**

### **Disclaimers**

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5069

---

**ARL-TR-4372****February 2008**

---

## **Characterization of Corrosion on Outdoor-Exposed Aluminum Metal-Matrix Composites as a Function of Reinforcement Specie and Volume Fraction**

**Ralph P. I. Adler and Daniel J. Snoha**  
**Weapons and Materials Research Directorate, ARL**

**George Hawthorn and Lloyd H. Hihara**  
**University of Hawaii**

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. <b>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</b>					
1. REPORT DATE (DD-MM-YYYY) February 2008		2. REPORT TYPE Final		3. DATES COVERED (From - To) June 2004–November 2006	
4. TITLE AND SUBTITLE Characterization of Corrosion on Outdoor-Exposed Aluminum Metal-Matrix Composites as a Function of Reinforcement Specie and Volume Fraction				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Ralph P. I. Adler, Daniel J. Snoha, George Hawthorn,* and Lloyd H. Hihara*				5d. PROJECT NUMBER M089 589131	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRD-ARL-WM-MC Aberdeen Proving Ground, MD 21005-5069				8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-4372	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES *Hawaii Corrosion Laboratory, Department of Mechanical Engineering, University of Hawaii at Manoa, Honolulu, HI 96826					
14. ABSTRACT The Hawaii Corrosion Laboratory and the U.S. Army Research Laboratory collaborated to prepare, environmentally expose for up to 2 years, and evaluate multivariant sets of metal matrix composites (MMCs). The experimental matrix involved variations in particulate volume-percent and particulate reinforcement specie (higher purity green and less-pure black silicon carbide, boron carbide, and alumina). The specific objective of this study was to determine, mainly using x-ray powder diffractometry, how observed gravimetric variations in corrosion behavior of these sets of MMCs (differentiated by four kinds of reinforcing agents with some variations in volume-percent), after relatively heavy-rainfall outdoor exposures in Hawaii, could be related to the crystallographic and morphological characteristics of the resulting corrosion products. Compared to the monolithic aluminum control specimens, the measured corrosion rates for these MMCs were considerably accelerated (by at least an order of magnitude) by the presence and relative amount of these second-phase particulates. The increased kinetics found for these MMCs were nominally proportional to the volume fraction of the particulate phase. Other differentials in gravimetric corrosion rates and corrosion product characteristics were related to the type of reinforcement phase present.					
15. SUBJECT TERMS corrosion, aluminum metal-matrix composites, silicon carbide, boron carbide, alumina, Bayerite					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT UNCLASSIFIED	b. ABSTRACT UNCLASSIFIED	c. THIS PAGE UNCLASSIFIED			Ralph P. I. Adler
			UL	52	19b. TELEPHONE NUMBER (Include area code) (410) 306-0826

---

## Contents

---

<b>List of Figures</b>	<b>v</b>
<b>List of Tables</b>	<b>vi</b>
<b>Acknowledgments</b>	<b>vii</b>
<b>1. Introduction</b>	<b>1</b>
<b>2. Experimental Materials and Sample Preparation</b>	<b>2</b>
2.1 MMC Specimens.....	2
2.2 Monolithic 6061-T6 Aluminum Alloy Control Specimens .....	3
<b>3. Experimental Procedures</b>	<b>3</b>
3.1 Outdoor-Exposure Corrosion Studies .....	3
3.1.1 Test Site, Corrosion-Exposure Racks, and Gravimetric Measurements .....	3
3.1.2 Outdoor-Exposure Specimens.....	4
3.2 X-ray Diffraction (XRD) Characterization of Corrosion Products .....	5
<b>4. Experimental Results</b>	<b>11</b>
4.1 Microstructural Observations.....	11
4.2 Gravimetric Observations.....	11
4.3 XRD Characterization Studies .....	11
4.3.1 Diffraction Scans for Unexposed Substrate Phases .....	11
4.3.2 Diffraction Scans for Exposed Samples With Substrate and Corrosion Product Phase .....	17
4.3.3 Phase Identification of the Corrosion Film on Exposed Substrates .....	18
<b>5. Discussion – Determining Corrosion Layer Thickness From X-ray Peak Attenuation Measurements</b>	<b>18</b>
5.1 Derivation of Thickness Determining Formula.....	18
5.2 Calculated Corrosion-Product Thickness.....	20
<b>6. Conclusions</b>	<b>23</b>
6.1 Outdoor-Exposure Corrosion Rates .....	23

6.2 Characterizing the Corrosion-Product Layers.....	24
<b>7. Summary</b>	<b>25</b>
<b>8. References</b>	<b>27</b>
<b>Distribution List</b>	<b>28</b>

---

## List of Figures

---

Figure 1. Typical arrangement of Al MMCs on outdoor-exposure rack at test site. ....	4
Figure 2. Before (left) and after (right) cleaning photos of 40 volume-percent SiC-reinforced Al MMC exposed for 90 days.....	5
Figure 3. XRD scan of virgin monolithic aluminum. ....	6
Figure 4. XRD scan of virgin 20-volume-percent black-SiC-reinforced Al MMC.....	7
Figure 5. XRD scan of virgin 50-volume-percent black-SiC-reinforced Al MMC.....	7
Figure 6. XRD scan of virgin 20-volume-percent B <sub>4</sub> C-reinforced Al MMC. ....	8
Figure 7. XRD scan of virgin 20-volume-percent Al <sub>2</sub> O <sub>3</sub> -reinforced Al MMC. ....	8
Figure 8. XRD scan of the front face of 50-volume-percent green-SiC-reinforced Al MMC after 12 months of outdoor exposure. ....	9
Figure 9. XRD scan of the front face of 50-volume-percent black-SiC-reinforced Al MMC after 12 months of outdoor exposure. ....	9
Figure 10. XRD scan of the front face of 20-volume-percent B <sub>4</sub> C-reinforced Al MMC after 12 months of outdoor exposure.....	10
Figure 11. XRD scan of the front face of 20-volume-percent Al <sub>2</sub> O <sub>3</sub> -reinforced Al MMC after 12 months of outdoor exposure.....	10
Figure 12. Microstructure of virgin 50-volume-percent green-SiC-reinforced Al MMC. ....	11
Figure 13. Microstructure of virgin 50-volume-percent black-SiC-reinforced Al MMC. ....	12
Figure 14. Microstructure of virgin 20-volume-percent black-SiC-reinforced Al MMC. ....	12
Figure 15. Microstructure of virgin 20-volume-percent B <sub>4</sub> C-reinforced Al MMC.....	13
Figure 16. Microstructure of virgin 20-volume-percent Al <sub>2</sub> O <sub>3</sub> -reinforced Al MMC.....	13
Figure 17. Linear x-ray-intensity absorption model. ....	19
Figure 18. Corrosion film x-ray-intensity absorption model adapted to diffraction geometry. ...	20

---

## List of Tables

---

Table 1. Resistivities of selected materials.....	1
Table 2. Composition of 6061 and 6092 aluminum alloys.....	3
Table 3. Gravimetric measurements (cleaned specimens).....	14
Table 4. Gravimetric measurements (uncleaned specimens).....	14
Table 5. XRD peak intensities for virgin and exposed 6061 aluminum and Al-SiC MMC specimens.....	15
Table 6. XRD peak intensities for virgin and exposed Al-B <sub>4</sub> C MMC specimens.....	16
Table 7. XRD peak intensities for virgin and exposed Al-Al <sub>2</sub> O <sub>3</sub> MMC specimens.....	16
Table 8. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed 6061 aluminum and Al-SiC MMC specimens. ....	21
Table 9. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed Al-B <sub>4</sub> C MMC specimens.....	21
Table 10. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed Al-Al <sub>2</sub> O <sub>3</sub> MMC specimens.....	22
Table 11. Comparative values (from averaged diffraction peak results) of corrosion product thickness after 12 months of outdoor exposure. ....	22



---

## **Acknowledgments**

---

The authors are grateful for the support from the Pacific Rim Corrosion Research Program under U.S. Army contract DAAE30-03-C-1071 administered through the Army Corrosion Office (by Robert Zanolwicz, John Theis, and Dr. Joseph Argento), located at Picatinny Arsenal, NJ. We also thank our colleagues at the Hawaii Corrosion Laboratory and the U.S. Army Research Laboratory for their administrative and technical support.

INTENTIONALLY LEFT BLANK.

---

## 1. Introduction

---

The promising metallurgical concept of incorporating stiff ceramic fiber as reinforcements into metallic matrices to produce metal-matrix composites (MMCs) with enhanced properties relative to the monolithic metal has been well demonstrated by academia and industry. However, there has been relatively less concern that the presence of such second (reinforcing) phases could have some compositional (due to electrochemical differences), physical (e.g., large differences in electrical resistivity among the ceramic phases, see table 1), and microstructural effects on corrosion phenomena and associated kinetics.

Table 1. Resistivities of selected materials.

Material	Resistivity ( $\Omega$ cm)	Temperature ( $^{\circ}$ C)	Notes	Reference
B <sub>4</sub> C	$10^1$	—	Pure	(1)
SiC	$10^{-5}$ – $10^{13}$	—	Dependant on purity	(2)
Al <sub>2</sub> O <sub>3</sub>	$>10^{14}$	30	99.7%	(3)
TiO <sub>2</sub>	$10^{13}$ – $10^{18}$	25	99.6%	(4)

Numerous MMC components with continuous or discontinuous reinforcing fibers and particulates (silicon carbide [SiC], boron carbide [B<sub>4</sub>C], and alumina [Al<sub>2</sub>O<sub>3</sub>]), primarily with aluminum alloy (Al) matrices, are already being produced for various applications (5). Al-SiC MMCs are generally used in structural and electronic applications, while Al-B<sub>4</sub>C MMCs and Al-Al<sub>2</sub>O<sub>3</sub> MMCs are generally used in structural applications. Each type of reinforcement constituent possesses certain advantages and disadvantages. Of these Al MMCs, those with SiC reinforcements are the most prevalent. In structural applications, low-purity black SiC is used at loadings between 15 and 25 volume-percent. In electronic-packaging applications (5), the major function of the SiC, whose reinforcement content ranges from ~30–55 volume-percent, is to reduce the MMC coefficient of thermal expansion to values closer to those of electronic-component materials such as gallium arsenide. In electronic-grade MMCs, high-purity green SiC is preferred for its high thermal conductivity. The green SiC also possesses high electrical resistivity and should be less likely to promote any galvanic corrosion of the aluminum matrix as compared to black SiC that, because it is less pure, has a lower resistivity. B<sub>4</sub>C has some advantages over SiC in that it is 20% lighter, improves MMC weldability, and is good for neutron shielding (5). The relatively low electrical resistivity (6) of B<sub>4</sub>C ( $10^{-1}$ – $10^1$   $\Omega$  cm) may promote galvanic corrosion in MMCs. Al<sub>2</sub>O<sub>3</sub> reinforcements have the advantage of being an insulator ( $>10^{14}$   $\Omega$  cm) and, thus, should not promote galvanic corrosion with the aluminum matrix. However, the density of Al<sub>2</sub>O<sub>3</sub> (6) is more than 20% higher than that of SiC, resulting in a heavier MMC for the same volume-fraction reinforcement.

The primary concern, with respect to the corrosion durability of Al MMCs, is that galvanic corrosion may occur when the incorporated particles or fibers are conductive or semiconductive (7, 8). The galvanic effect of a conductor such as graphite has been generally accepted; whereas, galvanic effects of the nonmetallic components such as SiC, a semiconductor with resistivities ranging from  $10^{-5}$  to  $10^{13}$   $\Omega$  cm, depending on its purity (2, 9), are in question. Theoretically, when aluminum is coupled with an insulating component such as  $\text{Al}_2\text{O}_3$ , there should be no galvanic effects.  $\text{B}_4\text{C}$  has a relatively low resistivity ( $\sim 1$   $\Omega$  cm), and, therefore, galvanic coupling is likely. For the SiC-reinforced MMCs, the current Hawaii Corrosion Laboratory (HCL) scanning vibrating electrode technique and scanning ion-selective electrode technique results also indicate a galvanic effect (10). First, there are similar characteristics on the current density maps and pH profiles over the localized corrosion regions that formed on 20-volume-percent  $\text{B}_4\text{C}$  and 20-volume-percent SiC Al MMCs. Second, the corrosion behavior of 20-volume-percent  $\text{Al}_2\text{O}_3$  Al MMC is different from that of the 20-volume-percent  $\text{B}_4\text{C}$  and 20-volume-percent SiC Al MMCs. Third, the extent of corrosion of 20-volume-percent SiC-reinforced Al MMC was lower than that of the 20-volume-percent  $\text{B}_4\text{C}$ -reinforced Al MMC. That the extent of corrosion of these three MMCs decreased with increasing reinforcement resistivities indicates that galvanic effects accelerated the corrosion process.

Accordingly, the specific objective of this study was to determine the impact of the relative volume fraction and reinforcement specie on the bulk corrosion rates of discontinuously reinforced Al MMCs relative to a comparable monolithic aluminum alloy after outdoor exposures at the highest rainfall (HCL test site at the Lyon Arboretum on Oahu). Further characterizations of crystallographic and morphological features of the resulting corrosion products, acquired mainly using x-ray powder diffractometry techniques, were used to obtain correlations with the gravimetric results.

---

## 2. Experimental Materials and Sample Preparation

---

### 2.1 MMC Specimens

The discontinuously reinforced aluminum MMCs were fabricated by DWA Aluminum Composites (Chatsworth, CA) using nominally identical processing and thermomechanical histories to avoid differences in corrosion behavior associated with processing inconsistencies. Each custom MMC lot was fabricated using DWA's proprietary powder metallurgy and hot-pressing processing operation forming nominally 3.7-in-diameter billets that were then heat treated to the T6 condition. The chemical composition of the 6092 aluminum alloy matrix is listed in table 2. Corrosion disk samples, nominally 0.1 in thick, were cut from the billet by electrical discharge machining (EDM) followed by abrasive grit-blasting to remove the recast layer induced by EDM thermal effects.

Table 2. Composition of 6061 and 6092 aluminum alloys.

Alloy	Solute Concentrations (Volume-Percent Solute by Element)							
	Si	Fe	Cu	Mn	Mg	Cr	Zn	Ti
6061 Al	0.4–0.8	0.7	0.15–0.4	0.15	0.8–1.2	0.04–0.35	0.25	0.15
6092 Al	0.75	0.09	0.83	NA	1.05	NA	NA	0.05

Note: NA = not applicable.

The MMC particulate reinforcements were green and black SiC, B<sub>4</sub>C, and Al<sub>2</sub>O<sub>3</sub>. The black SiC volume fractions were 5, 10, 20, 40, and 50 volume-percent, the green SiC was 50 volume-percent, and the B<sub>4</sub>C and Al<sub>2</sub>O<sub>3</sub> were 20 volume percent. However, only the 20- and 50-volume-percent black SiC samples were selected for this study to determine the effect of SiC volume fraction on corrosion behavior. The 20-volume-percent series of black SiC, B<sub>4</sub>C, and Al<sub>2</sub>O<sub>3</sub> MMCs compared the effect of reinforcement resistivity on corrosion behavior; likewise for the MMCs with 50-volume-percent black and green SiC.

## 2.2 Monolithic 6061-T6 Aluminum Alloy Control Specimens

The control samples were nominally 2- × 2- × 0.125-in coupons machined from wrought sheet stock. The 6061 aluminum alloy composition, listed in table 2, was a close match to the powder-metallurgy-produced 6092 aluminum alloy's composition.

# 3. Experimental Procedures

## 3.1 Outdoor-Exposure Corrosion Studies

### 3.1.1 Test Site, Corrosion-Exposure Racks, and Gravimetric Measurements

MMC and control specimens were exposed to a heavy-rainfall atmospheric test site located in the Lyon Arboretum on the island of Oahu. The Lyon Arboretum site is on University of Hawaii (UH) property. Test-site maintenance (including changing chloride candles, downloading weather data, photography, and/or retrieving specimens) was performed on a monthly basis.

Test racks were designed and constructed using 316 stainless steel and Trex\* materials. Trex is a wood-like composite made from recycled wood chips and recycled polyethylene. Test racks on UH had Trex slats on a stainless-steel frame. For this corrosion study, the MMC and monolithic specimens were exposed at 30° from the horizontal, and each specimen was secured with three nylon insulators.

\* Trex is a registered trademark of Trex Company, Inc.

### 3.1.2 Outdoor-Exposure Specimens

Each MMC disk (0.1 in thick and ranging in diameter from 3.56 to 3.75 in) was stamped with an alphanumeric code using a Telisis Benchmark 320 pin-stamping system. The disks were washed in acetone, followed by ultrasonic cleaning in deionized water. After drying, each specimen was weighed on a Mettler AE163 electronic balance. The initial weight of each specimen was measured in grams to four decimal places. Figure 1 shows a typical arrangement of the MMC specimens on a test rack.

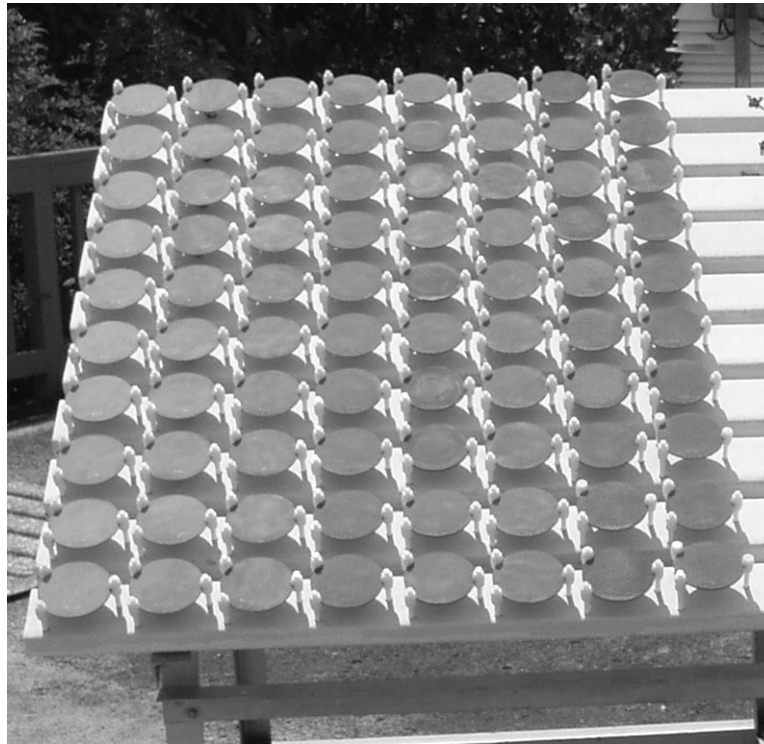


Figure 1. Typical arrangement of Al MMCs on outdoor-exposure rack at test site.

Samples of the eight lots of MMCs were arranged in eight columns of 10 rows, where each column contained the same type of MMC. Specimens were placed on the rack with the alphanumeric code on the underside (facing down and heretofore referred to as the back face). Whenever MMC or control specimens were recovered from the field, they were scanned or photographed in the uncleaned state. The disks used for bulk gravimetric corrosion measurements were then cleaned in a solution of phosphoric acid ( $\text{H}_3\text{PO}_4$ ), chromium trioxide ( $\text{CrO}_3$ ), and ultrapure ( $18.1 \text{ M}\Omega \text{ cm}$ ) water as described in ISO 8407 (11). The remaining disks were stored for further analyses and for characterizing the corrosion products.

For the cleaning operation, specimens were immersed in the just-described mildly heated phosphoric acid/chromium trioxide/water solution for 10 min at a temperature between 90 and 100 °C. They were then ultrasonically cleaned for 30 min in deionized water. After oven drying at 21 °C for 20–30 min, the specimens were reweighed on the same Mettler balance to determine weight loss. The initial and final weights were used, along with the surface area of each specimen to calculate the average weight loss per unit area for each MMC sample. The reported weight-loss data was the average value from two replicate samples; the data was reported as an average corrosion rate as grams per square meter per day (gmd). Figure 2 shows a macrograph of the front (upward facing, environmentally exposed) surface of a specimen before and after cleaning.

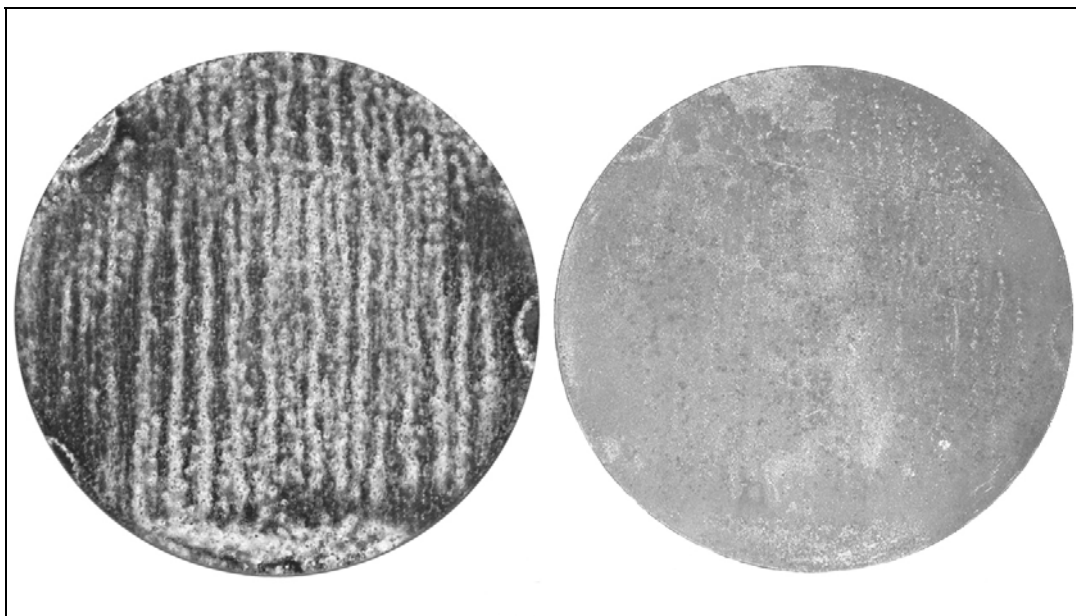


Figure 2. Before (left) and after (right) cleaning photos of 40 volume-percent SiC-reinforced Al MMC exposed for 90 days.

In addition to the MMCs at the Lyon test site, 10 6061 aluminum control specimens were also exposed for the same durations in order to obtain a nominal baseline corrosion weight loss per unit area of a monolithic alloy with a similar composition as the MMC matrix phase. The aluminum coupons, measuring  $2 \times 2 \times 0.125$  in, were stamped, cleaned, and weighed in the same manner as the eight reinforced MMC sample sets.

### 3.2 X-ray Diffraction (XRD) Characterization of Corrosion Products

XRD techniques were used as the major characterization procedure. The primary (metal matrix and ceramic reinforcement) phases were readily identifiable from prominent diffraction scan peak locations for each MMC and monolithic control sample. Comparing the differences between diffraction scans for the matched set of unexposed (virgin) samples with the exposed samples provided information about the nature of the corrosion product that overlies the original

substrate. Also, by measuring the decrement in the peak intensities of some major diffraction lines from the aluminum alloy substrate, calculations to determine the thickness of the oxide corrosion product layer were made. Similarly, the increase in the relative background count level of the exposed sample relative to the matched virgin sample provided another empirical measure of the overlying oxide thickness. Details about the Debye-Scherrer method to identify phases and the basic physics of x-ray absorption used to calculate the overlying oxide thickness can be found in Cullity (12). Specific details about calculating the thickness of an overlying surface layer of corrosion product from the peak intensity ratios of the exposed and virgin pair of samples will be presented subsequently.

A Philips Analytical powder diffraction system with a model PW1820 vertical goniometer and a copper target x-ray tube was used to collect diffraction scans from the Al MMC and monolithic aluminum control specimens. The goniometer was arranged with a  $1^\circ$  fixed divergence slit and a 0.2-mm receiving slit and operated in the step-scan mode with a  $0.02^\circ 2\theta$  (diffraction angle) step size and a 2-s/step count time. The diffraction scans were acquired over a  $2\theta$  range of  $20^\circ$ – $110^\circ$  with the x-ray generator set at 45 kV and 40 mA. Philips X'Pert software was used for data collection and search-match analysis, with the candidate lines (peaks) compared against the International Centre for Diffraction Data (ICDD) Powder Diffraction File\* for phase identification. Please note in figures 3–11 that the diffracted intensity is plotted as counts squared to emphasize the presence of low-intensity peaks. Also, the diffraction scans are displayed only for the  $20^\circ$ – $70^\circ 2\theta$  range to enhance visualization of the x-ray peaks that were used for intensity-ratio calculations.

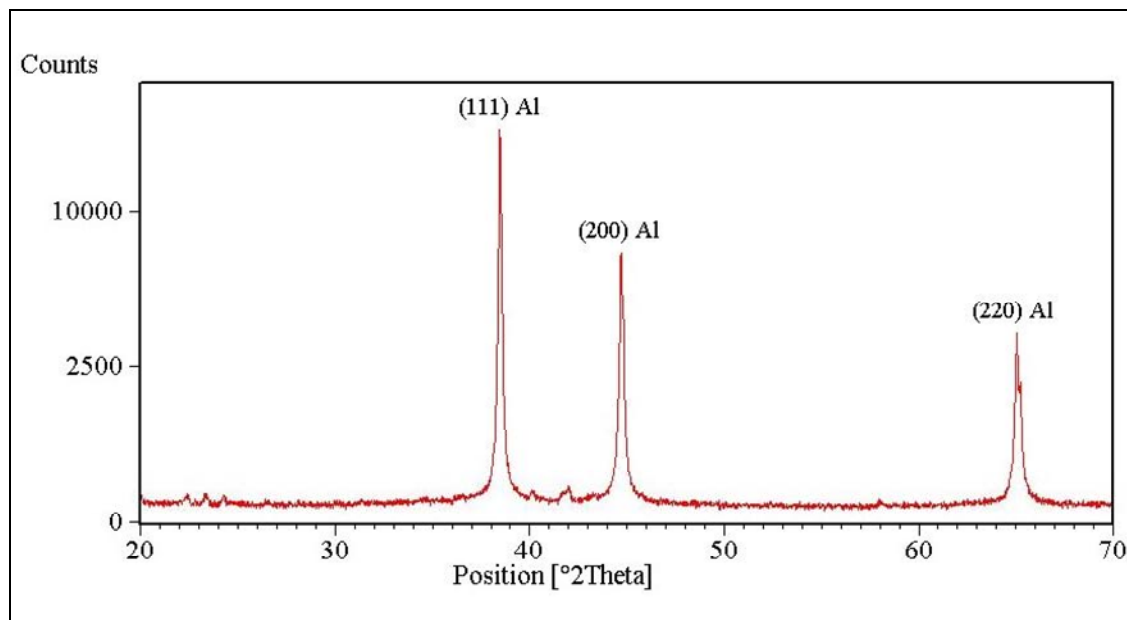


Figure 3. XRD scan of virgin monolithic aluminum.

\* Powder Diffraction File is a trademark of JCPDS-International Center for Diffraction Data.



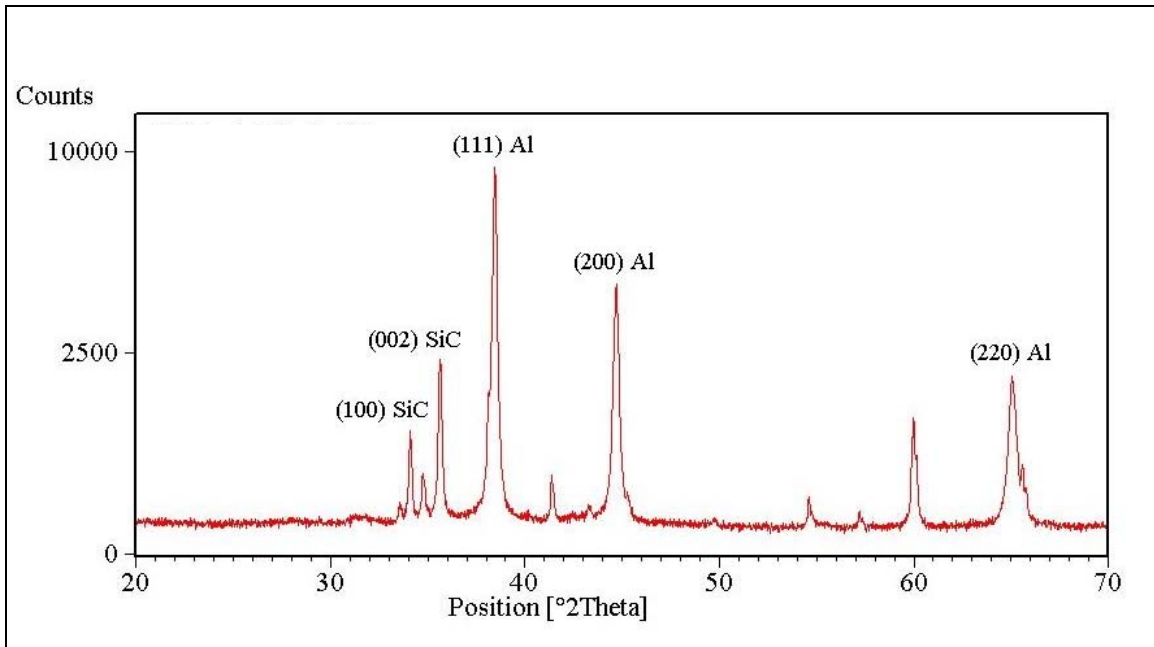


Figure 4. XRD scan of virgin 20-volume-percent black-SiC-reinforced Al MMC.

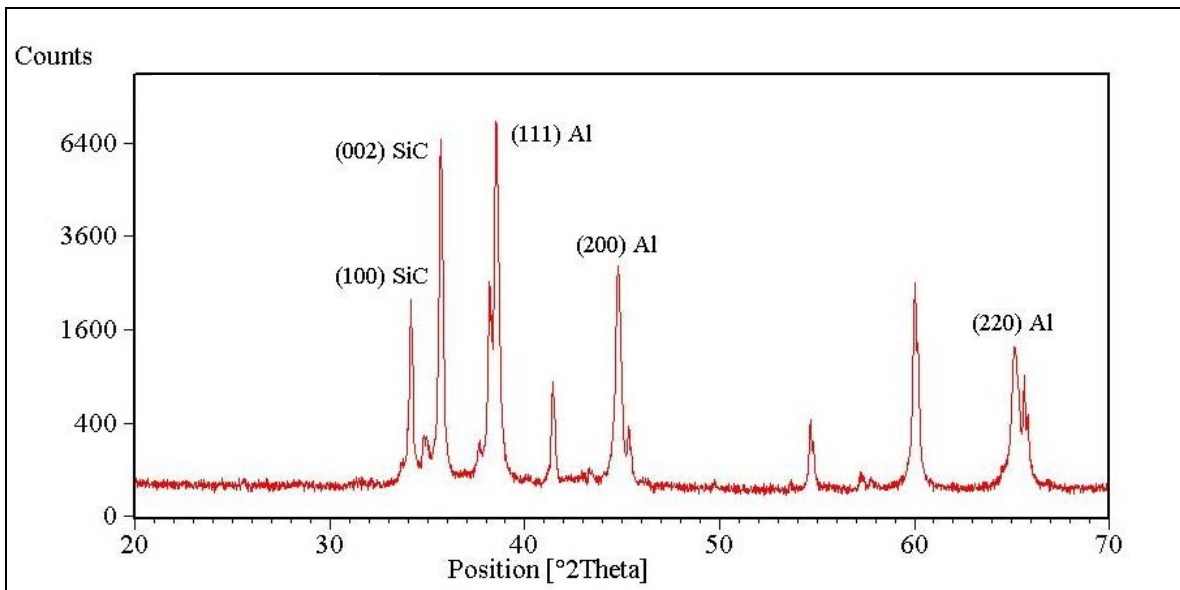


Figure 5. XRD scan of virgin 50-volume-percent black-SiC-reinforced Al MMC.

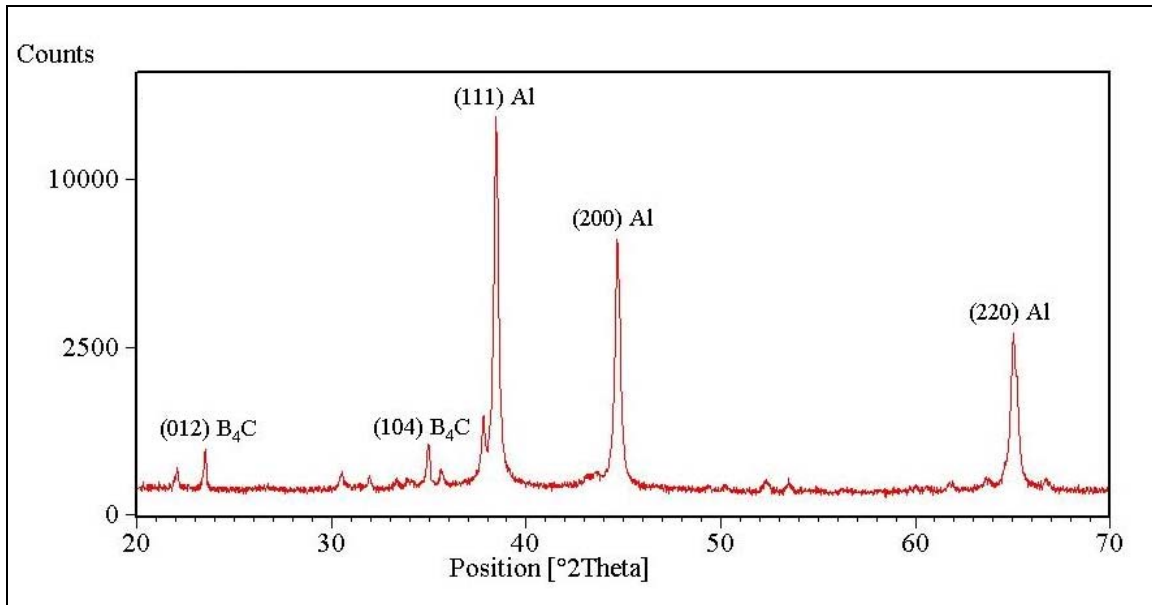


Figure 6. XRD scan of virgin 20-volume-percent B<sub>4</sub>C-reinforced Al MMC.

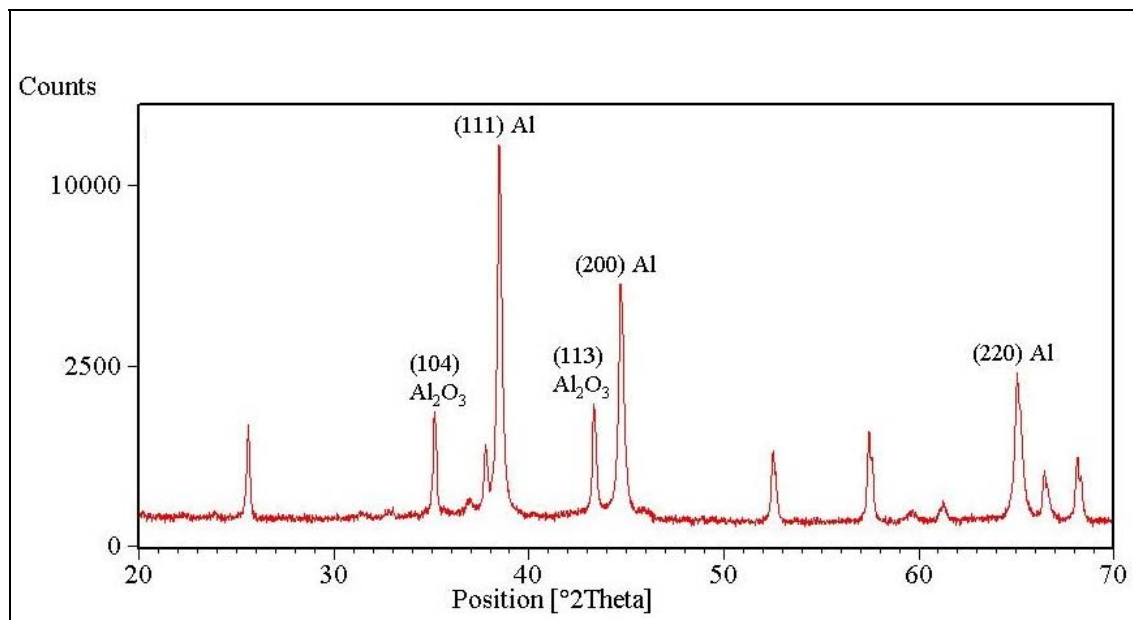


Figure 7. XRD scan of virgin 20-volume-percent Al<sub>2</sub>O<sub>3</sub>-reinforced Al MMC.

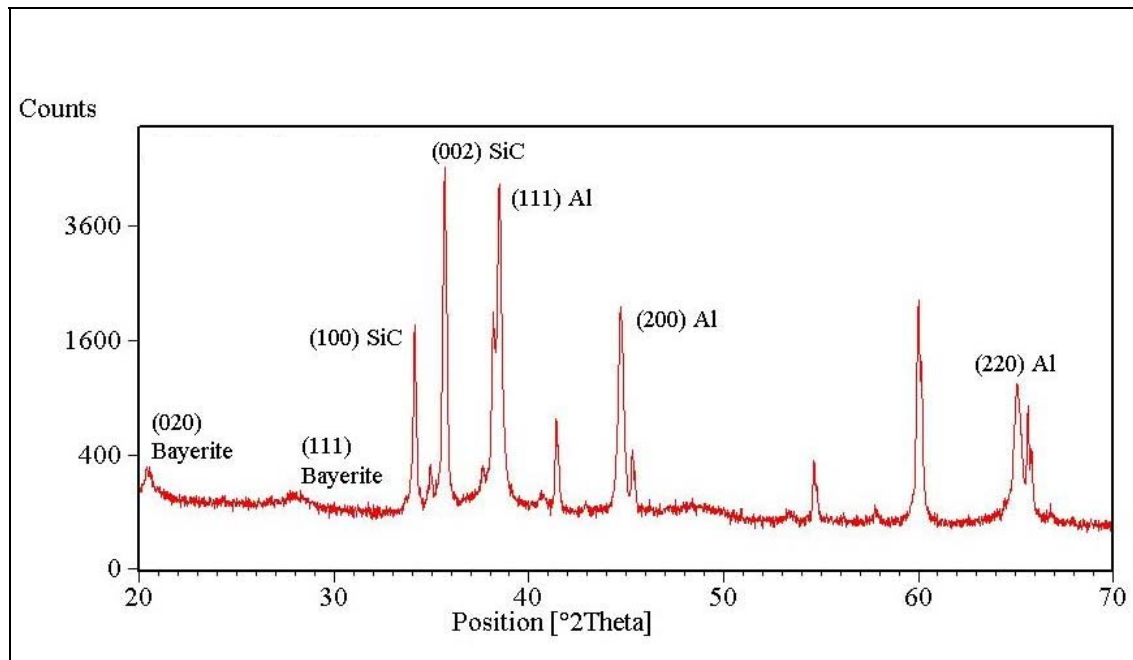


Figure 8. XRD scan of the front face of 50-volume-percent green-SiC-reinforced Al MMC after 12 months of outdoor exposure.

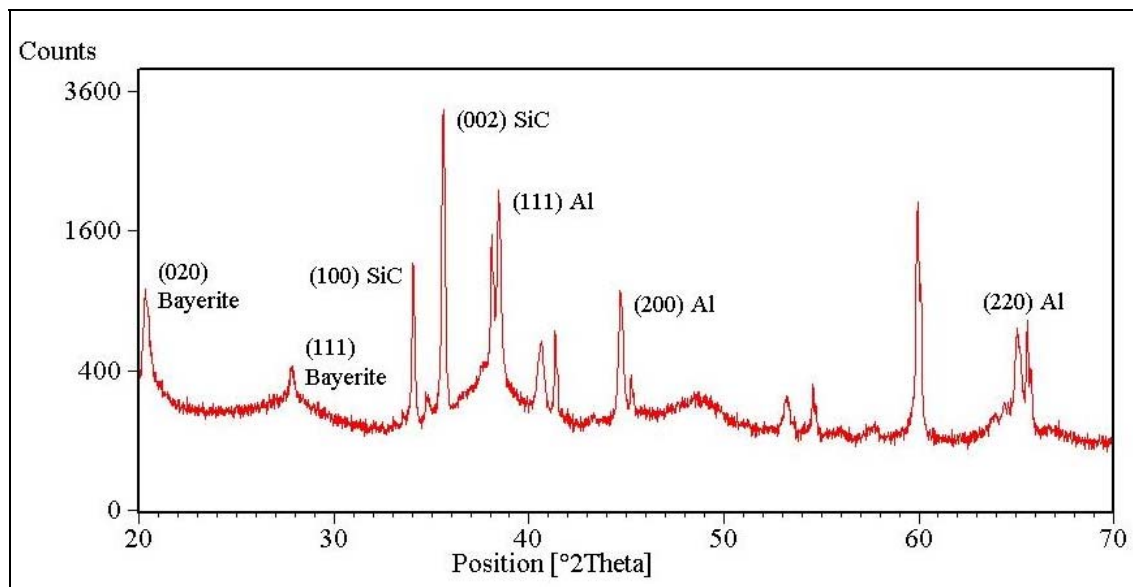


Figure 9. XRD scan of the front face of 50-volume-percent black-SiC-reinforced Al MMC after 12 months of outdoor exposure.

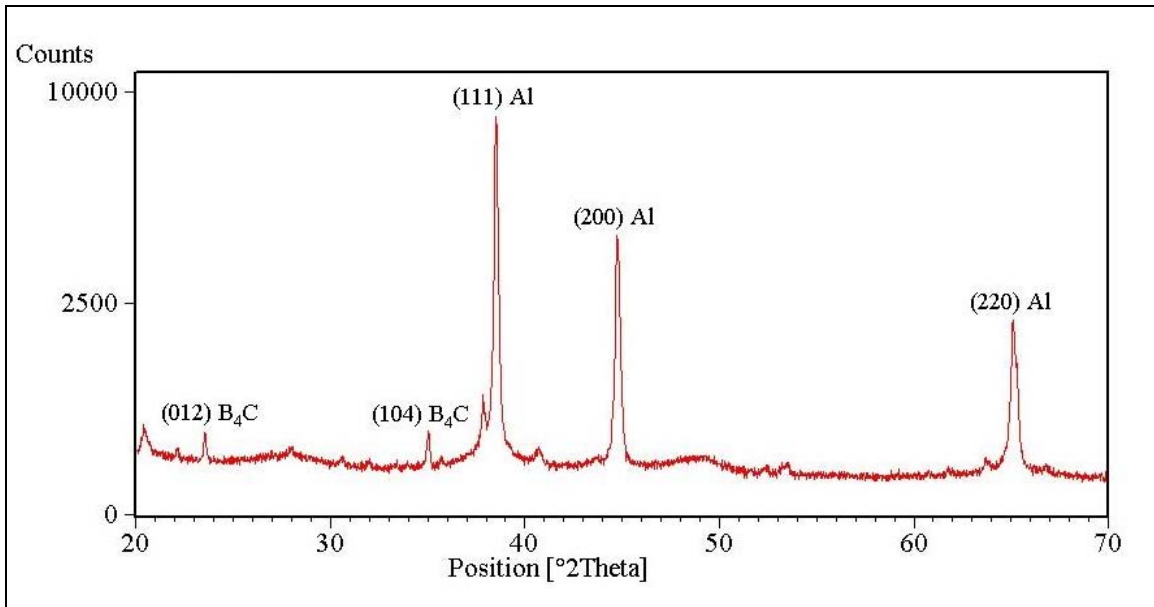


Figure 10. XRD scan of the front face of 20-volume-percent  $B_4C$ -reinforced Al MMC after 12 months of outdoor exposure.

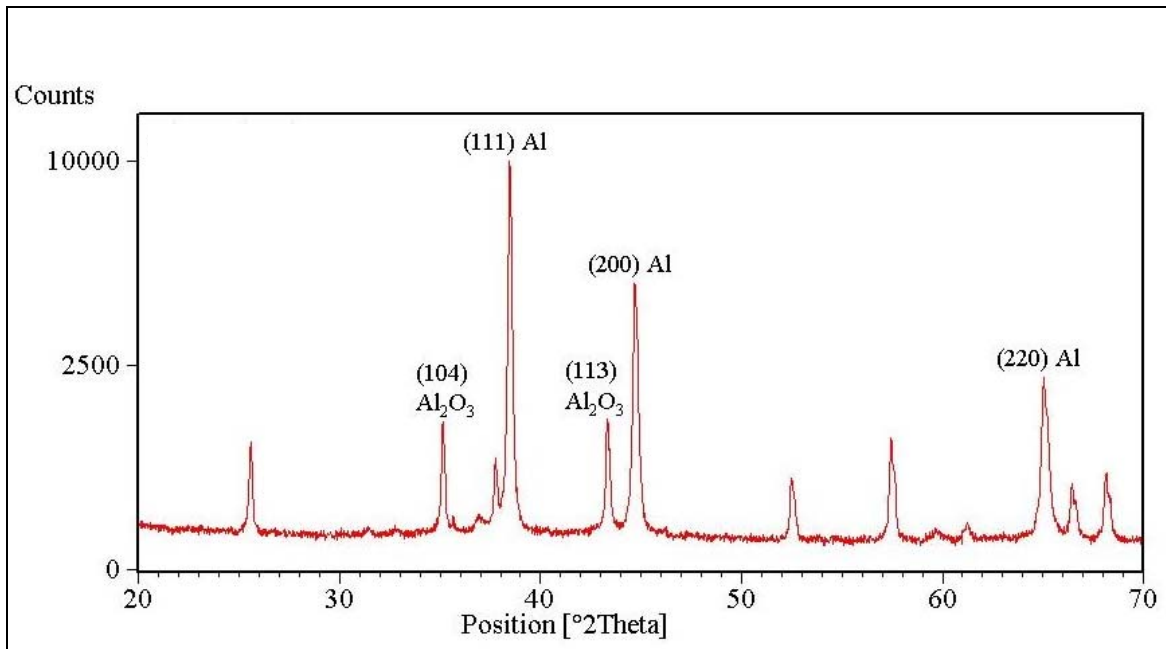


Figure 11. XRD scan of the front face of 20-volume-percent  $Al_2O_3$ -reinforced Al MMC after 12 months of outdoor exposure.

---

## 4. Experimental Results

---

### 4.1 Microstructural Observations

The microstructure of virgin samples is shown in figures 12–16. The various microstructures of these MMCs show the discontinuous arrangement of particles and the difference in particle sizes dependent on the volume-percent of the MMC.

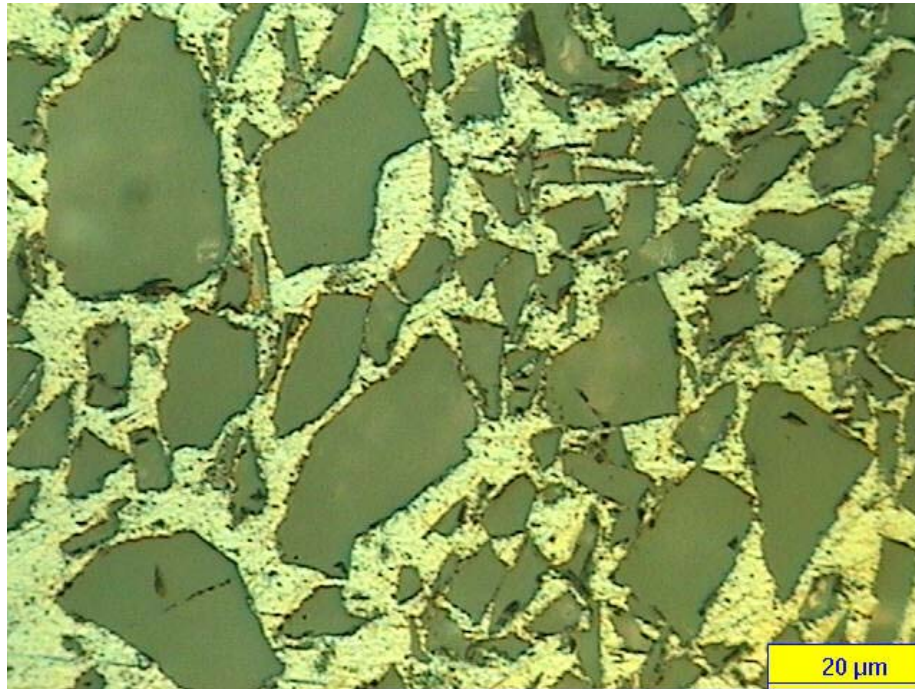


Figure 12. Microstructure of virgin 50-volume-percent green-SiC-reinforced Al MMC.

### 4.2 Gravimetric Observations

Tables 3 and 4 list the UH site gravimetric data for the 1-year weight-loss results from cleaned samples, as well as the weight gains for uncleaned characterization samples for the aluminum control samples, the 20- and 50-volume-percent black-SiC samples, the 50-volume-percent green-SiC sample, and the 20-volume-percent B<sub>4</sub>C and Al<sub>2</sub>O<sub>3</sub> samples.

### 4.3 XRD Characterization Studies

#### 4.3.1 Diffraction Scans for Unexposed Substrate Phases

Typical diffraction scans for virgin samples of the control coupon (figure 3) and two different black-SiC (20 and 50 volume-percent) MMCs are shown in figures 4 and 5. The phase-analysis software identified the primary phases (Al and SiC) in the unexposed substrate. The Miller indices (hkl) and intensities of the corresponding prominent peaks from all the SiC-reinforced



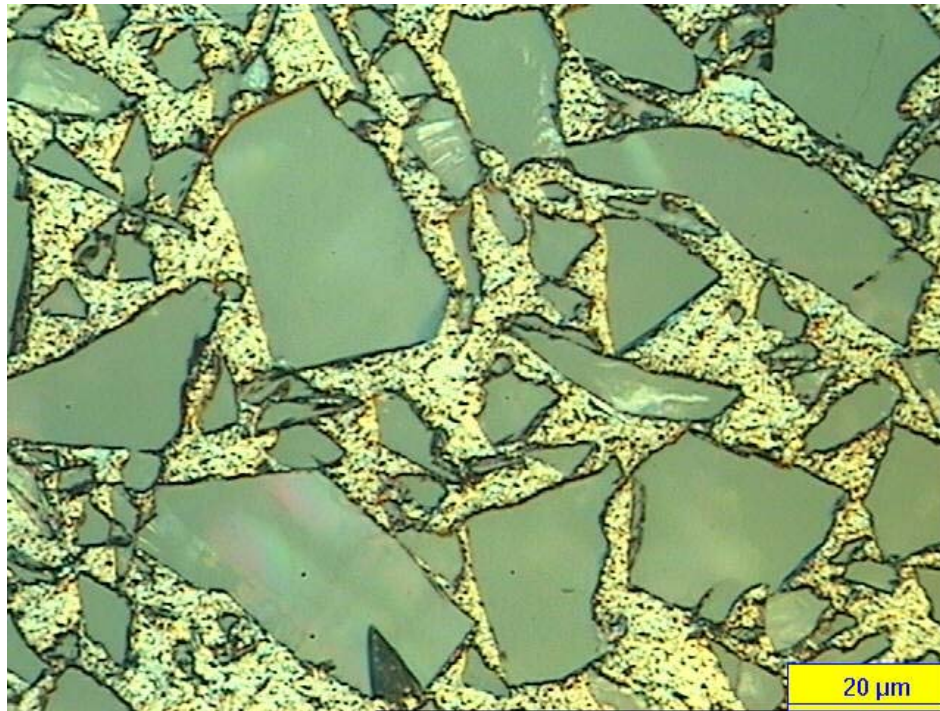


Figure 13. Microstructure of virgin 50-volume-percent black-SiC-reinforced Al MMC.

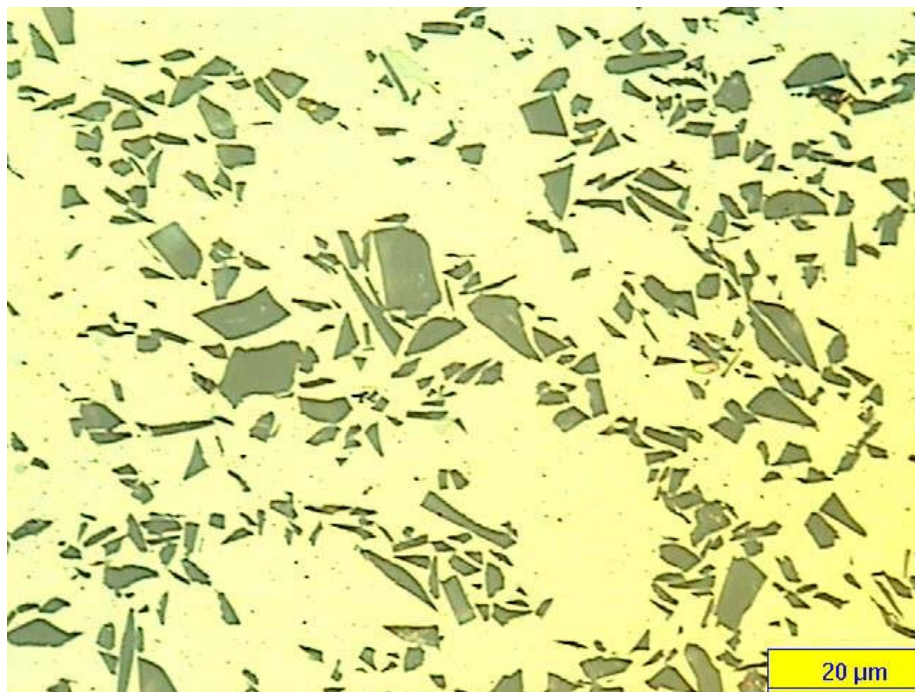


Figure 14. Microstructure of virgin 20-volume-percent black-SiC-reinforced Al MMC.

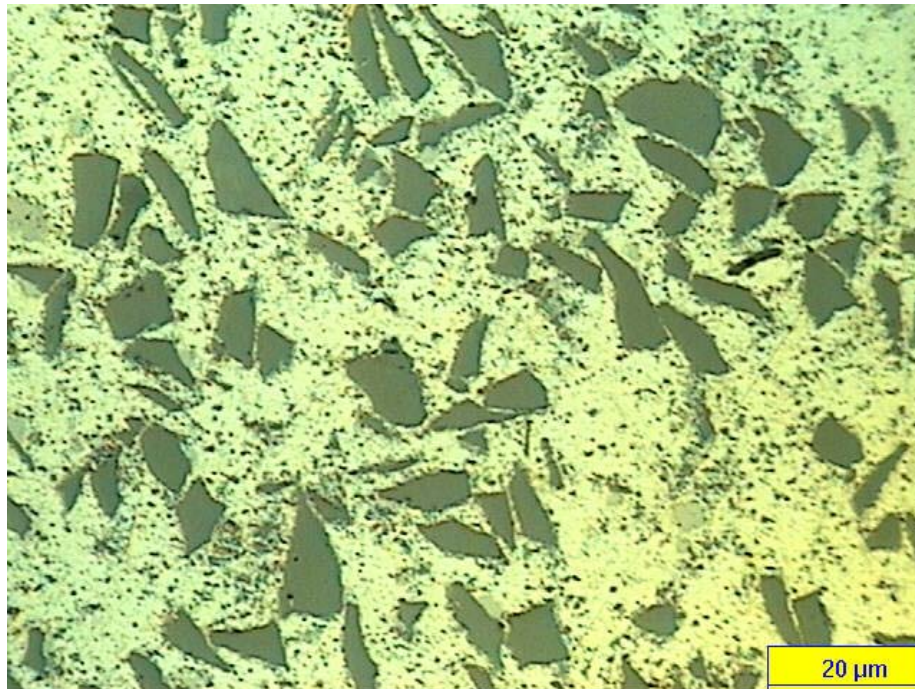


Figure 15. Microstructure of virgin 20-volume-percent B<sub>4</sub>C-reinforced Al MMC.

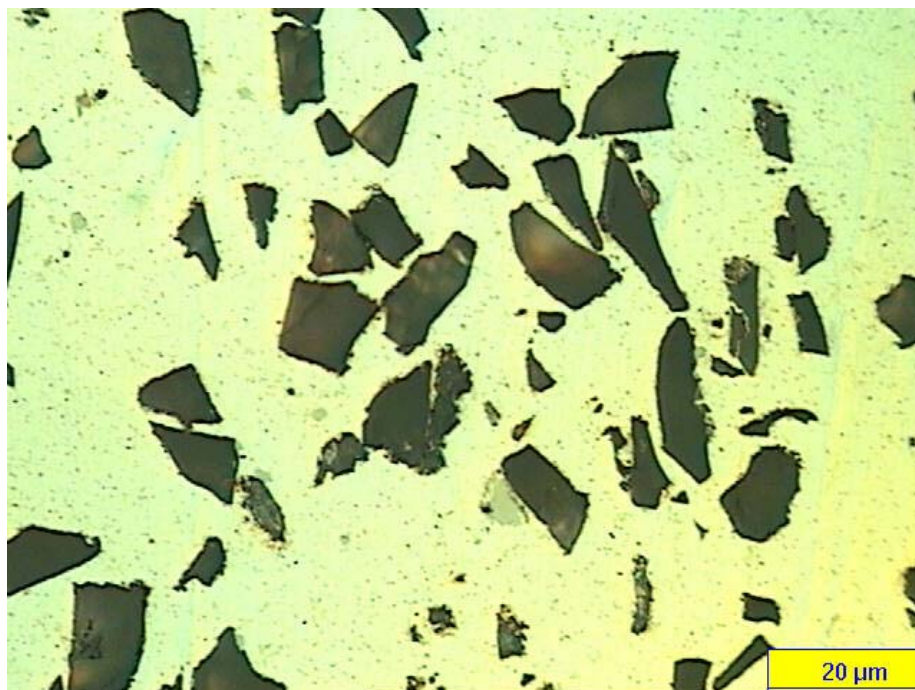


Figure 16. Microstructure of virgin 20-volume-percent Al<sub>2</sub>O<sub>3</sub>-reinforced Al MMC.



samples have been listed in table 5. Questionable or inconsistent data are marked with a question mark and ndl indicates that no diffraction line was present for that phase. Note that compared to the corresponding diffraction peaks from the monolithic control sample, the intensities from the aluminum-matrix peaks are reduced and, in general, are inversely proportional to the volume-percent of the SiC phase present in that MMC. The corresponding increase in all the SiC peak intensities is, again, generally proportional to the amount of SiC phase present in each MMC. Typical diffraction scans for virgin samples of the two other 20-volume-percent MMC variants with B<sub>4</sub>C and Al<sub>2</sub>O<sub>3</sub> reinforcements are shown in figures 6 and 7. The phase-analysis software identified the primary phases in the unexposed substrate as aluminum and boron carbide or aluminum and corundum. The Miller indices and intensities of the corresponding prominent peaks for these MMCs have been listed in tables 6 and 7, respectively.

Table 3. Gravimetric measurements (cleaned specimens).

Specimen	Initial Weight (g)	Final Weight (g)	Change in Weight (g)	Average Change (g)	Corrosion Rate (gmd)
6061 Al (monolithic)	21.4056	21.4039	0.0017	0.0021	0.00097261
	21.4343	21.4319	0.0024		
6092 Al 20-volume-percent black SiC	47.7314	47.6657	0.0657	0.0641	0.01234878
	47.7186	47.6562	0.0624		
6092 Al 50-volume-percent black SiC	49.1076	48.6768	0.4308	0.3785	0.07176491
	49.1702	48.8441	0.3261		
6092 Al 50-volume-percent green SiC	48.5586	48.3209	0.2377	0.2377	0.04739349
6092 Al 20-volume-percent B <sub>4</sub> C	44.8217	44.4436	0.3781	0.3249	0.06161030
	44.9342	44.6625	0.2717		
6092 Al 20-volume-percent Al <sub>2</sub> O <sub>3</sub>	47.9893	47.8255	0.1638	0.1711	0.03469962
	48.0114	47.8330	0.1784		

Table 4. Gravimetric measurements (uncleaned specimens).

Specimen	Initial Weight (g)	Final Weight (g)	Change in Weight (g)	Surface Area (cm <sup>2</sup> )	Weight Change /Unit Area (g/cm <sup>2</sup> )
6061 Al (monolithic)	21.4323	21.4368	0.0045	51.613	0.000087
6092 Al 20-volume-percent black SiC	47.7455	47.8077	0.0622	137.245	0.000453
6092 Al 50-volume-percent black SiC	49.2496	49.8476	0.5980	137.987	0.004333
6092 Al 50-volume-percent green SiC	47.3706	47.6614	0.2908	131.342	0.002214
6092 Al 20-volume-percent B <sub>4</sub> C	44.7391	45.0951	0.3560	137.028	0.002598
6092 Al 20-volume-percent Al <sub>2</sub> O <sub>3</sub>	48.0078	48.1658	0.1580	130.080	0.001215



Table 5. XRD peak intensities for virgin and exposed 6061 aluminum and Al-SiC MMC specimens.

Specimen	Months Exposed	Face	Bayerite Phase		SiC Phase		Al Phase			Background Intensity at 23° 2 $\theta$
			(020) hkl, 20.3° 2 $\theta$	(111) hkl, 27.8° 2 $\theta$	(100) hkl, 34.1° 2 $\theta$	(002) hkl, 35.7° 2 $\theta$	(111) hkl, 38.5° 2 $\theta$	(200) hkl, 44.7° 2 $\theta$	(220) hkl, 65° 2 $\theta$	
6061 Al (monolithic)	0	Front	Ndl	Ndl	Ndl	Ndl	15751	7476	3668	38
		Back	—	—	—	—	—	—	—	—
	6	Front	Ndl	Ndl	Ndl	Ndl	13515	3439	7613 ?	40
		Back	Ndl	Ndl	Ndl	Ndl	15686	7161	4882 ?	38
	12	Front	Ndl	Ndl	Ndl	Ndl	14042	6166	5183 ?	37
		Back	Ndl	Ndl	Ndl	Ndl	11131	8001 ?	4729 ?	32
6092 Al 20-volume-percent black SiC	0	Front	Ndl	Ndl	888	2245	9228	4446	1873	62
		Back	Ndl	Ndl	873	2193	9170	5040	1850	62
	12	Front	Ndl	Ndl	847 ?	2340 ?	9790 ?	3106	1694	65
		Back	Ndl	Ndl	775	2410 ?	9983 ?	3440	1610	69
6092 Al 50-volume-percent black SiC	0	Front	Ndl	Ndl	2085	6354	7157	2687	1190	44
		Back	—	—	—	—	—	—	—	—
	6	Front	37	16	1838	5707	6028	2420	1102	110
		Back	95	50	2276 ?	6557 ?	5258	2106	935	102
	12	Front	772	192	1147	3069	1923	792	519	140
		Back	128	28	2088 ?	5627	5378	2003	1035	103
6092 Al 50-volume-percent green SiC	0	Front	Ndl	Ndl	2351	6674	6248	2800	1232	51
		Back	—	—	—	—	—	—	—	—
	12	Front	169	41	1756	4830	4422	1984	800	140
		Back	67	19	2689 ?	6538	5420	2400	1084	90

Notes: Ndl = no diffraction line was present.

? = questionable or inconsistent data.

Table 6. XRD peak intensities for virgin and exposed Al-B<sub>4</sub>C MMC specimens.

Specimen	Months Exposed	Face	Bayerite Phase		B <sub>4</sub> C Phase		Al Phase			Background Intensity at 23° 2θ
			(020) hkl, 20.3° 2θ	(111) hkl, 27.8° 2θ	(012) hkl, 23.5° 2θ	(104) hkl, 35° 2θ	(111) hkl, 38.5° 2θ	(200) hkl, 44.7° 2θ	(220) hkl, 65° 2θ	
6092 Al 20-volume percent B <sub>4</sub> C	0	Front	Ndl	Ndl	326	378	13949	6408	2852	62
		Back	Ndl	Ndl	318	388	12990	6354	2547	60
	12	Front	293	74	175	234	8604	4048	2008	163
		Back	155	16	231	292	11080	5891	2311	69

Note: Ndl = no diffraction line was present.

Table 7. XRD peak intensities for virgin and exposed Al-Al<sub>2</sub>O<sub>3</sub> MMC specimens.

Specimen	Months Exposed	Face	Bayerite Phase		Al <sub>2</sub> O <sub>3</sub>		Al Phase			Background Intensity at 23° 2θ
			(020) hkl, 20.3° 2θ	(111) hkl, 27.8° 2θ	(104) hkl, 35.1° 2θ	(113) hkl, 43.3° 2θ	(111) hkl, 38.5° 2θ	(200) hkl, 44.7° 2θ	(220) hkl, 65° 2θ	
6092 Al 20-volume-percent Al <sub>2</sub> O <sub>3</sub>	0	Front	Ndl	Ndl	1348	1414	12129	5144	2263	65
		Back	Ndl	Ndl	1336	1437	12108	5413	2310	70
	12	Front	17	Ndl	1194	1267	9788	4800	2164	92
		Back	206	27	973	1166	7539	3648	1782	142

Note: Ndl = no diffraction line was present.

#### 4.3.2 Diffraction Scans for Exposed Samples With Substrate and Corrosion Product Phase

Typical diffraction scans from the front faces of the 12-month-exposed samples of the black and green SiC MMC variants are shown in figures 8 and 9, respectively. The phase-analysis software again identified the primary phases from the front and back faces of the exposed substrate as Al and SiC. Compared to the unexposed samples, the corresponding prominent peaks reappear but have attenuated intensities (see table 5). Typically, the attenuation of peak intensities from the back face is less than the front face. This observation can intuitively be interpreted (at least for the SiC-reinforced MMCs) that the corrosion film on the front face is thicker than that on the back face. Note the presence of two broad corrosion-product diffraction peaks labeled (020) Bayerite and (111) Bayerite that have been detected from the surfaces of the 50-volume-percent black and green SiC MMCs but are absent from the monolithic and 20-volume-percent SiC samples. Bayerite is a hydrated form of aluminum oxide with a density of  $\sim 3 \text{ g/cm}^3$ . It is remarkable that these Bayerite peak intensities are greater on the sample front face than on the back face by a factor of 3. Consistent with gravimetric data and the aluminum peak-intensity attenuation observations, it is not surprising that the intensities of the 50-volume-percent black-SiC Bayerite peaks are substantially greater than the 50-volume-percent green-SiC Bayerite peaks on either of the corresponding front or back surfaces. One can speculate that the appearance of the crystalline (020) and (111) Bayerite peaks represent some form of amorphous-to-crystalline transformation of the original Bayerite corrosion film, especially as the surface layer grows in thickness.

Typical diffraction scans from the front faces of 12-month-exposed samples of two 20-volume-percent MMC variants with  $\text{B}_4\text{C}$  and  $\text{Al}_2\text{O}_3$  reinforcements are shown in figures 10 and 11. The phase-analysis software again identified the primary phases as either aluminum and boron carbide or aluminum and corundum. The Miller indices and intensities of the corresponding prominent peaks for these MMCs from the front and back surfaces are listed in tables 6 and 7, respectively. Compared to the unexposed samples, the corresponding prominent peaks reappear but have attenuated intensities. For the boron-carbide MMC (and in common with the SiC MMC data), the attenuation of peak intensities from the back face being less than the front face and the presence of more intense Bayerite peaks diffracting from the front face should be noted. This combination of results leads to the interpretation that the corrosion film on the front face is much thicker than on the back face.

Counterintuitive results were detected for the alumina MMC. The attenuation of peak intensities from the front face being less than the back face, as well as the presence of more intense Bayerite peaks diffracting from the back face (see table 7), leads to the conflicting conclusion that the corrosion film on the back surface is thicker than on the front face, unlike the other sample results. Perhaps for the exposed alumina MMCs, solar irradiation might have impeded the corrosion process on the top surface; clearly, irradiation, climate, and humidity factors were

unchanged from the other (silicon-carbide- and boron-carbide-reinforced) MMC samples, since all of them were exposed for identical periods on the same rack.

#### **4.3.3 Phase Identification of the Corrosion Film on Exposed Substrates**

The original conceptual corrosion model for these environmentally exposed Al-MMC samples was that a semicontinuous film of corrosion product formed and chronologically grew in thickness over the substrate. The most likely oxidation product was some form of amorphous hydrated aluminum oxide since, in general, crystalline peaks of hydrated aluminum oxide were not detected by XRD on samples with environmental exposures of up to 6 months. In addition to the visually observed formation of a corrosion-product film on these samples, the XRD characterization results indicated that a substantial attenuation of the diffraction peaks from the primary aluminum and the crystalline reinforcement phase occurred and that there was a general increase of the overall low-angle background intensity values (arbitrarily measured at  $23^\circ 2\theta$ ), compared to the virgin counterpart samples, but it was not possible to determine the specific composition of this generic aluminum-oxide corrosion product. However, the increase in magnitude of this relative background intensity with exposure duration did track with the gravimetric data (see table 3), providing another indirect measure that the thickness of this amorphous corrosion layer was increasing with time. Fortunately, after 1 year, the detection of semicrystalline (020) and (111) Bayerite diffraction peaks for some MMC samples gave evidence that the originally formed amorphous phase was transforming into its crystalline state that was presumed to be of the same composition. Identifying Bayerite as the likely corrosion-film product will be used subsequently in corrosion-film-thickness calculations.

---

### **5. Discussion – Determining Corrosion Layer Thickness From X-ray Peak Attenuation Measurements**

---

#### **5.1 Derivation of Thickness Determining Formula**

In order to quantify the effect of the overlying corrosion layer on attenuating diffracted beam intensities, an equation to determine such thicknesses ( $t$ ) will be derived and adapted to the relevant diffractometer geometry. These calculations can be made by using the ratio of the diffracted peak ( $hkl$ ) intensity of the virgin ( $v$ ) sample  $I_D(hkl)_v$  to that of an exposed ( $e$ ) sample  $I_D(hkl)_e$ , along with handbook physical constants.

The first derivation is based on the generic linear attenuation absorption model (12). When x-rays with initial intensity  $I_0$  pass through a slab of absorbing material of thickness  $x$ , the resulting attenuation leads to a less-intense transmitted beam intensity  $I_x$ , as illustrated in figure 17. The relationship between the initial and the transmitted intensity is expressed in equation 1.

$$I_x = I_0 \exp[-(u/r)rx]. \quad (1)$$

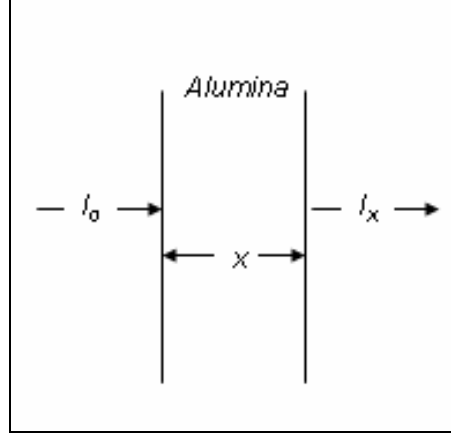


Figure 17. Linear x-ray-intensity absorption model.

The attenuation of the transmitted beam intensity, in addition to having a negative exponential relationship with the distance traversed in the absorbing layer, also is affected by the mass absorption coefficient ( $\mu/r$ ) and the density ( $r$ ) of that absorbing layer. Based on experimental insight for this x-ray characterization study that a corrosion layer formed on aluminum and Al-MMCs substrates, the value chosen for the alumina (or corundum) mass absorption coefficient was  $26.71 \text{ cm}^2/\text{g}$  and the density was nominally  $3 \text{ g/cm}^3$  (for Bayerite alumina with three waters of hydration; note that a range of values exist that are a function of the number of waters of hydration). These constants should approximately match those for hydrated alumina and were used in calculating nominal film thicknesses (even if not exact, they certainly provided a ranking order of calculated thicknesses as a function of time and sample characteristics). Thus, even if other values are subsequently chosen, only some recalculation will be required to adjust the absolute values; this will certainly not affect the generally observed trends that provide significant insight for this study.

These absorption calculations need to be adapted for the appropriate diffractometer geometry (12) used to record diffracted peak intensities, as indicated in figure 18. Note the following linear and geometrical relationships:

- thickness of the continuous alumina film =  $t$
- Bragg angle for (hkl) peak =  $2\theta$
- total x-ray absorption path length in film =  $x = 2y = 2t/\sin\theta$ .

For the usual diffractometer geometry, the intensity diffracted by peak (hkl),  $I_D(\text{hkl})$ , can be determined using equation 1 by inserting the total absorbing path length,  $x$ ,

$$I_D(\text{hkl}) = I_0 \exp[-(\mu/r)rx] = AI_0 \exp[-(\mu/r)r2t/\sin\theta] , \quad (2)$$

where  $A$  = diffraction intensity correction factor for each (hkl) peak.

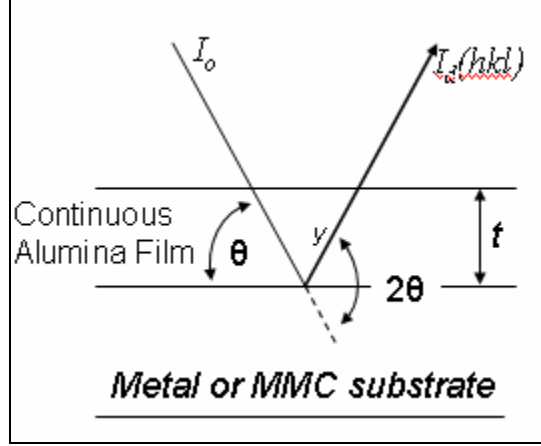


Figure 18. Corrosion film x-ray-intensity absorption model adapted to diffraction geometry.

For unexposed (virgin, v) samples where there is no corrosion overlayer ( $t = 0$ ), equation 2 becomes

$$I_D(hkl)_v = A(hkl)I_0 \quad (3)$$

After outdoor exposure (e), an oxide film of thickness  $t$ , forms, so that equation 2 now becomes

$$I_D(hkl)_e = A(hkl)I_0 \exp[-(u/r)2t/\sin\theta]. \quad (4)$$

The corrosion product thickness  $t$ , is solved for from the ratio of equations 3 and 4,

$$t = \ln[I_D(hkl)_v/I_D(hkl)_e] \sin\theta / [2(u/r)r]. \quad (5)$$

## 5.2 Calculated Corrosion-Product Thickness

Equation 5 was used to calculate the corrosion-product thicknesses for all the samples exposed for 1 year. The results for major diffraction peaks from the aluminum matrix and the respective reinforcement phases have been listed in tables 8–10.

Caveats for these measurements and calculations (that depend explicitly on the ratio of a series of single (hkl) peak intensity values but taken at different times) need to be outlined to explain a certain amount of variability/uncertainty apparent in these tables. First, it should be noted that the standard deviation for the accuracy of this data can be as high as 50%, especially when peak intensities are low, resulting in small, statistically undesirable peak-to-background ratios (12). This was the systematic case for certain weakly diffracting reinforcing phases, where only one or two major peak-intensity values were used for calculating thicknesses. Additionally, equipment-related factors can also produce small systematic or random drifts in incident radiation intensity, due to equipment and power supply variations; these in turn affect the exact magnitude of the measured diffracted peak intensities during an individual diffraction scan. Then there can be local variations in sample microstructure and corrosion rate variables (with kinetics that vary by

Table 8. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed 6061 aluminum and Al-SiC MMC specimens.

Specimen	Months Exposed	Face	Peak Intensity		Thickness of Corrosion Product (μm)					Background Intensity at 23° 2θ
			Bayerite Phase		SiC Phase		Al Phase			
			(020) hkl, 20.3° 2θ	(111) hkl, 27.8° 2θ	(100) hkl, 34.1° 2θ	(002) hkl, 35.7° 2θ	(111) hkl, 38.5° 2θ	(200) hkl, 44.7° 2θ	(220) hkl, 65° 2θ	
6061 Al (monolithic)	0	Front	Ndl	Ndl	Ndl	Ndl	—	—	—	38
		Back	—	—	—	—	—	—	—	—
	12	Front	Ndl	Ndl	Ndl	Ndl	2.4	4.5	?	37
		Back	Ndl	Ndl	Ndl	Ndl	7.1	?	?	32
6092 Al 20-volume-percent black SiC	0	Front	Ndl	Ndl	—	—	—	—	—	62
		Back	Ndl	Ndl	—	—	—	—	—	62
	12	Front	Ndl	Ndl	?	?	?	10.2	3.2	65
		Back	Ndl	Ndl	?	?	?	7.8	4.8	69
6092 Al 50-volume-percent black SiC	0	Front	Ndl	Ndl	—	—	—	—	—	44
		Back	—	—	—	—	—	—	—	—
	12	Front	772	192	?	13.9	27	28.8	27.8	140
		Back	128	28	?	2.3	5.9	6.9	4.7	103
6092 Al 50-volume-percent green SiC	0	Front	Ndl	Ndl	—	—	—	—	—	51
		Back	—	—	—	—	—	—	—	—
	12	Front	169	41	?	6.2	7.1	8.1	14.5	140
		Back	67	19	?	0.39	2.9	2.8	4.3	90

Notes: Ndl = no diffraction line was present.

? = questionable or inconsistent data.

Table 9. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed Al-B<sub>4</sub>C MMC specimens.

Specimen	Months Exposed	Face	Peak Intensity		Thickness of Corrosion Product (μm)					
			Bayerite Phase		B <sub>4</sub> C Phase		Al Phase			Background Intensity at 23° 2θ
			(020) hkl, 20.3° 2θ	(111) hkl, 27.8° 2θ	(012) hkl, 23.5° 2θ	(104) hkl, 35° 2θ	(111) hkl, 38.5° 2θ	(200) hkl, 44.7° 2θ	(220) hkl, 65° 2θ	
6092 Al 20-volume-percent B <sub>4</sub> C	0	Front	Ndl	Ndl	—	—	—	—	—	62
		Back	Ndl	Ndl	—	—	—	—	—	60
	12	Front	293	74	7.8	9.2	9.2	10.7	9.9	163
		Back	155	16	4.2	5.1	4	1.9	5.2	69

Note: Ndl = no diffraction line was present.

Table 10. Corrosion product thickness as a function of XRD peak intensity attenuations for virgin and exposed Al-Al<sub>2</sub>O<sub>3</sub> MMC specimens.

Specimen	Months Exposed	Face	Peak Intensity		Thickness of Corrosion Product (μm)					
			Bayerite Phase		Al <sub>2</sub> O <sub>3</sub> Phase		Al Phase			Background Intensity at 23° 2θ
			(020) hkl, 20.3° 2θ	(111) hkl, 27.8° 2θ	(104) hkl, 35.1° 2θ	(113) hkl, 43.3° 2θ	(111) hkl, 38.5° 2θ	(200) hkl, 44.7° 2θ	(220) hkl, 65° 2θ	
6092 Al 20-volume-percent Al <sub>2</sub> O <sub>3</sub>	0	Front	Ndl	Ndl	—	—	—	—	—	65
		Back	Ndl	Ndl	—	—	—	—	—	70
	12	Front	17	Ndl	2.2	2.7	4.4	2.2	1.9	92
		Back	206	27	6.1	4.6	9.7	8.7	8.4	142

Note: Ndl = no diffraction line was present.

Table 11. Comparative values (from averaged diffraction peak results) of corrosion product thickness after 12 months of outdoor exposure.

Specimen	Weight Gain /Unit Area (g/cm <sup>2</sup> )	Face	Nominal Value Over SiC Particles (μm)	Nominal Value Over B <sub>4</sub> C Particles (μm)	Nominal Value Over Al <sub>2</sub> O <sub>3</sub> Particles (μm)	Nominal Value Over Al Matrix (μm)
6061 Al (monolithic)	0.000087	Front	Ndl	Ndl	Ndl	3
		Back	Ndl	Ndl	Ndl	7 ?
6092 Al 20-volume-percent black SiC	0.000453	Front	?	Ndl	Ndl	9
		Back	?	Ndl	Ndl	7
6092 Al 50-volume-percent black SiC	0.004333	Front	13.9 ?	Ndl	Ndl	28
		Back	2.3	Ndl	Ndl	6
6092 Al 50-volume-percent green SiC	0.002214	Front	6.2	Ndl	Ndl	9
		Back	0.4 ?	Ndl	Ndl	3
6092 Al 20-volume-percent B <sub>4</sub> C	0.002598	Front	Ndl	8.5	Ndl	10
		Back	Ndl	4.7	Ndl	3
6092 Al 20-volume-percent Al <sub>2</sub> O <sub>3</sub>	0.001215	Front	Ndl	Ndl	2.5	3
		Back	Ndl	Ndl	5.4	9

Notes: Ndl = no diffraction line was present.

? = questionable or inconsistent data.



a factor of 2 for samples in the same environment not being unusual) that further complicate the experimental data.

Despite these caveats, in general, the thickness values track consistently with the gravimetrically determined weight-change values as summarized in table 11, where averaged diffraction peak results from the aluminum matrix and the reinforcement phases after a 1-year exposure are presented. Except for the 20-volume-percent  $\text{Al}_2\text{O}_3$  MMC with a thicker corrosion product layer on the back face, the reinforced Al-MMC samples had a thicker corrosion layer on the front, upward facing surface, with by far the thickest being the 28- $\mu\text{m}$  layer present on the 50-volume-percent black SiC MMC, followed by three others in the 7–10- $\mu\text{m}$  range. The corresponding back-face thicknesses ranged from 3 to 6  $\mu\text{m}$  and were not consistent with the gravimetric trends. It was also interesting to note that the front-face corrosion-product thickness over the silicon-carbide particles was about 1/2 of that over the aluminum matrix, while the corrosion-product thicknesses over the reinforcing boron carbide and alumina particles were slightly less but similar to that over the aluminum matrix. (Further surface examination will be required to determine whether there is some continuity of the corrosion layer over the reinforcement particles or whether, if there is no local coverage, it is an artifact produced by the absorption of x-rays passing at a diffraction angle  $\theta$  through the corrosion product growing above the adjacent aluminum-matrix phase). For the 20-volume-percent reinforcement phase series, the boron-carbide MMC had a thicker front-face corrosion layer than the silicon-carbide MMC (both based on gravimetric and film-thickness results). The alumina-reinforced MMC with the intermediate gravimetric result and the contrary presence of a thinner front face and a thicker back-face corrosion layer will clearly need to be investigated further.

---

## **6. Conclusions**

---

### **6.1 Outdoor-Exposure Corrosion Rates**

Although this report covers observations from only a limited set of monolithic and Al-MMC samples subjected to 1 year of atmospheric exposure at a single (but climatologically the wettest) HCL location, some trends are clearly visible from the gravimetric corrosion data. For comparable exposure times, all of these MMCs have a corrosion rate that is at least an order of magnitude greater than a similar monolithic aluminum alloy. The bulk corrosion rate of MMCs reinforced with black SiC generally increases with an increase in volume fraction of the reinforcement. This increase in corrosion rate appears to be (more than linearly) proportional to the volume fraction of the SiC (where the gravimetric rate for 50-volume-percent SiC MMC is at least  $5\times$  greater than the 20-volume-percent SiC MMC even though the 50-volume-percent SiC sample presented 1/3 less aluminum-matrix-phase surface area to react). Also, the corrosion rate for the 50-volume-percent black-SiC MMC was about twice that of the 50-volume-percent green-SiC MMC that is of higher purity and higher resistivity. This would be expected because of galvanic action if the black SiC supports cathodic currents. However, the 50-volume-percent

green SiC had a higher corrosion rate than the 20-volume-percent black-SiC MMC, indicating that reinforcement phase content was also significant.

Of the three 20-volume-percent MMCs with different reinforcement species, the B<sub>4</sub>C MMC generally corroded at a higher rate than those reinforced with either Al<sub>2</sub>O<sub>3</sub> (with an intermediate rate) or SiC (with the lowest rate). Also, the 20-volume-percent B<sub>4</sub>C MMC with significantly less reinforcement phase had a higher corrosion rate than the 50-volume-percent green SiC. This trend is also likely due in part to the resistivity of the reinforcements, since B<sub>4</sub>C generally has low resistivity, SiC has wide fluctuations in resistivity depending on purity, and Al<sub>2</sub>O<sub>3</sub> is an insulator. Although there is a trend for the corrosion rate to increase with increased reinforcement content, there is now strong evidence that the type of reinforcing phase can strongly influence the atmospheric corrosion rate of that MMC. Thus, those MMCs with higher resistivity reinforcement particles tend to have comparably lower corrosion rates.

These outdoor-exposure tests generally support the hypothesis that corrosion is related to the conductivity and the volume fraction of the reinforcement specie. Corrosion rates increased as the content of black SiC was increased. For the same volume fractions, the corrosion rates were lower in MMCs reinforced with high-purity green SiC than for those with black SiC. Corrosion rates were higher for MMCs reinforced with B<sub>4</sub>C than they were for MMCs reinforced with equal amounts of either SiC or Al<sub>2</sub>O<sub>3</sub>.

## **6.2 Characterizing the Corrosion-Product Layers**

Experimental XRD data for virgin and exposed samples of the control coupon and the five MMC variants yielded quantitative and qualitative characterization of the atmospheric corrosion products that formed on these samples during their 1-year outdoor exposure. Further analysis using intensity ratios of the virgin and exposed samples provided semiquantitative measures of the corrosion-product thickness.

For the exposed samples, the relative intensities of the aluminum and the reinforcement diffraction peaks decrease significantly relative to those from their comparable virgin samples. The attenuation of the peak-intensity values was found to be somewhat proportional to the thickness of corrosion product that formed over the original substrate. Typically, for all but the exposed 20-volume-percent alumina MMC sample, the observed attenuation of the peak-intensity values was greater for XRD scans obtained from the front (upward facing) surfaces than from the back surfaces of each sample, indicating that the front surface had a thicker corrosion product. By far, the largest corrosion-layer thickness (28 μm) was calculated for the front surface of the 50-volume-percent black-SiC MMC, and this was consistent with the gravimetric data—three of the other four reinforced MMCs were in the 9–10-μm range. Nearly all of the back surfaces had 3–6-μm thicknesses, with the exception of the anomalous 20-volume-percent alumina MMC sample with 3- and 9-μm front and back thicknesses, respectively.

For the XRD scans from the monolithic control and the 20-volume-percent black-SiC MMC samples exposed for 1-year, peak-intensity attenuations resulted in peaks that were nominally 80% of those from virgin samples, with no evidence of a crystalline-hydrated aluminum oxide-phase. Thus, it was concluded that the overlying corrosion product that caused the observed peak-intensity attenuations was due to the presence of a semicontinuous hydrated aluminum oxide layer that also increased the low-angle background intensities. But since no crystalline-hydrated aluminum-oxide diffraction peaks were detected, the attenuation was attributed to an overlying amorphous Bayerite corrosion-product layer.

Most of the rest of the exposed samples' XRD scans had greater peak-intensity attenuations consistent with the presence of thicker corrosion-product layers. In addition, all of these XRD scans (including the anomalous 20-volume-percent alumina MMC sample) had two other distinct general features that were metrified (see tables 8–10): the background levels of XRD scans were elevated (the arbitrary values reported were for the background intensity at  $2\theta = 23^\circ$ , chosen because no overlapping crystalline peaks appeared in any XRD scan), and the presence of semicrystalline alumina namely, (020) Bayerite and (111) Bayerite diffraction peaks that appeared as a crystalline peaks (with measurable peak intensities that proved to be a good metric) emerging from an amorphous hump. These metrics qualitatively tracked well with and were inversely proportional to the attenuation of the substrate phase(s) diffraction peak intensities, thus, indirectly substantiating the corrosion-product-thickness calculation results.

---

## 7. Summary

---

In general, this corrosion-product characterization study provided important insights into procedures for measuring Al MMC corrosion. It is intuitively obvious that corrosion phenomena and kinetics on the front and back faces of outdoor-corrosion specimens should be different, and this study has quantified these differences. In most cases, the thickness of the corrosion-product layer on the front surface exceeds that on the back surface since environmental effects such as solar irradiation and/or the extended presence of water/electrolyte films should be greater on the upward facing sample face. However, the caveat is that bulk gravimetric measurements of corrosion (rates) only represent the weighted average of the phenomena occurring on the upward facing and back surfaces. Thus, care in interpreting any gravimetric corrosion measurement results is recommended.

The case for the anomalous reversal of thicknesses on front and back surfaces of the 20-volume-percent alumina MMC sample deserves further study to confirm whether the results are repeatable. If this phenomenon is real, fundamental studies should be undertaken to discover what physical phenomena in the reinforcement phase can impede and/or accelerate corrosion kinetics. One can speculate that for this specific MMC, the presence or absence of solar irradiation may affect the properties of certain forms of crystalline  $\text{Al}_2\text{O}_3$  that, in turn, may alter the kinetics and/or mechanism of Al-MMC corrosion.

For applications that consider utilizing Al-MMCs components for their superior mechanical properties, appropriate regard should be taken for the lowered environmental durability of these materials relative to monolithic aluminum alloys. This limitation can be compensated for by designing in greater thicknesses for that component or by using suitable corrosion-mitigating coatings or other surface treatments.

---

## 8. References

---

1. Ceradyne, Inc. Home Page. <http://www.ceradyne.com> (accessed April 2002).
2. Ichinose, N. *Introduction to Fine Ceramics*; Wiley: New York, NY, 1987; pp 50–52.
3. Bolz, R. E.; Tuve, G. L. *CRC Handbook of Tables for Applied Engineering Science, 2nd Ed.*; CRC Press: Boca Raton, FL, 1973; pp 262–264.
4. Goodfellow Corp. *Metals and Materials Catalog*; Oakdale, PA, 1991–1992.
5. DWA Aluminum Composites Home Page. <http://www.dwa-dra.com> (accessed May 2003).
6. Goodfellow Corp. Technical Data Sheet. <http://www.goodfellow.com> (accessed May 2003).
7. Hihara, L. H. Corrosion of Metal Matrix Composites. *Corrosion: Materials, Environments, and Industries*; American Society of Metals International: Materials Park, OH, 2005.
8. Hihara, L. H. Metal-Matrix Composites. In *Manual on Corrosion Tests and Standards: Application and Interpretation, 2nd Ed.*; American Society for Testing and Materials International: West Conshohocken, PA, 2005.
9. Wylie, R. G. *Humidity and Moisture*. Wexler, A., Ed.; Reinhold Publishing Corp.: New York, NY, 1964; p 507.
10. Hongbo, D.; Hihara, L. H. Localized Corrosion Currents and pH Profile over B<sub>4</sub>C, SiC, and Al<sub>2</sub>O<sub>3</sub> Reinforced 6092 Aluminum Composites in 0.5M Na<sub>2</sub>SO<sub>4</sub> Solution. *Journal of the Electrochemical Society* **2005**, 152, (4).
11. ISO 8407. *Corrosion of Metals and Alloys – Removal of Corrosion Products from Corrosion Test Specimens* **1991**.
12. Cullity, B. D. *Elements of X-Ray Diffraction, 2nd Ed.*; Addison-Wesley: Reading, MA, 1978.

NO. OF  
COPIES ORGANIZATION

1 DEFENSE TECHNICAL  
(PDF INFORMATION CTR  
ONLY) DTIC OCA  
8725 JOHN J KINGMAN RD  
STE 0944  
FORT BELVOIR VA 22060-6218

1 US ARMY RSRCH DEV &  
ENGRG CMD  
SYSTEMS OF SYSTEMS  
INTEGRATION  
AMSRD SS T  
6000 6TH ST STE 100  
FORT BELVOIR VA 22060-5608

1 DIRECTOR  
US ARMY RESEARCH LAB  
IMNE ALC IMS  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRD ARL CI OK TL  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

ABERDEEN PROVING GROUND

1 DIR USARL  
AMSRD ARL CI OK TP (BLDG 4600)

NO. OF  
COPIES ORGANIZATION

1 DIRECTOR  
US ARMY RSRCH LAB  
AMSRD ARL SE DE  
R ATKINSON  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

2 DIRECTOR  
US ARMY RSRCH LAB  
AMSRD ARL WM MB  
M BERMAN  
M CHOWDHURY  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1 COMMANDER  
US ARMY MATERIEL CMD  
AMXMI INT  
9301 CHAPEK RD  
FORT BELVOIR VA 22060-5527

2 PM MAS  
SFAE AMO MAS MC  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM D  
J LUTZ  
BLDG 354  
PICATINNY ARSENAL NJ  
07806-5000

1 DEPT OF THE ARMY  
RDECOM ARDEC  
AMSRD AAR EMO F  
BLDG 1  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM  
M PALATHINGAL  
BLDG 65 SOUTH  
PICATINNY ARSENAL NJ  
07806-5000

NO. OF  
COPIES ORGANIZATION

1 US ARMY ARDEC  
AMSTA AR CCH A  
F ALTAMURA  
BLDG 354  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSTA AR CCH A  
R HOWELL  
BLDG 65 NORTH  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSTA AR CCH A  
L MANOLE  
BLDG 65 SOUTH  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM L  
A VELLA  
BLDG 354  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM L  
D VO  
BLDG 65 SOUTH  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM T  
M NICOLICH  
BLDG 65 SOUTH  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEM  
M LUCIANO  
BLDG 65 SOUTH  
PICATINNY ARSENAL NJ  
07806-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	US ARMY ARDEC AMSRD AAR AEM S MUSALLI BLDG 65 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR EBM R CARR BLDG 1 PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC SFAE AMO MAS SETI T C LIVECCHIA BLDG 354 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR AEM L M YOUNG BLDG 65 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR AEM C D DEMELLA BLDG 61 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR AEM S CHICO BLDG 65 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC SFAE AMO MAS LC D RIGOGLIOSO BLDG 354 M829E3 IPT PICATINNY ARSENAL NJ 07806-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	US ARMY ARDEC AMSRD AAR AEM L P DONADIA BLDG 65 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSTA AR CCH B K HENRY BLDG 95 PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR AEM L F DONLON BLDG 65 SOUTH PICATINNY ARSENAL NJ 07806-5000
1	PM MAS SFAE AMO MAS PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC SFAE AMO MAS LC P VALENTI BLDG 354 PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC AMSRD AAR AEM L R SAYER BLDG 65 PICATINNY ARSENAL NJ 07806-5000
1	US ARMY ARDEC SFAE AMO MAS LC F CHANG BLDG 354 PICATINNY ARSENAL NJ 07806-5000



<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	PM ARMS AMSRD AAR EMB J BRESCIA BLDG 1 PICATINNY ARSENAL NJ 07806-5000
1	PM MAS SFAE AMO MAS CHIEF ENGINEER PICATINNY ARSENAL NJ 07806-5000
1	PM MAS SFAE AMO MAS PS PICATINNY ARSENAL NJ 07806-5000
2	PM MAS SFAE AMO MAS LC PICATINNY ARSENAL NJ 07806-5000
1	COMMANDER US ARMY TACOM AMSTA SF WARREN MI 48397-5000
1	COMMANDER US ARMY TACOM PM COMBAT SYSTEMS SFAE GCS CS 6501 ELEVEN MILE RD WARREN MI 48397-5000
2	OFC OF NAVAL RSRCH J CHRISTODOULOU D SHIFLER ONR CODE 332 800 N QUINCY ST ARLINGTON VA 22217-5600
1	COMMANDER US ARMY TACOM PM SURVIVABLE SYSTEMS SFAE GCSS W GSI H M RYZYI 6501 ELEVEN MILE RD WARREN MI 48397-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	COMMANDER US ARMY TACOM CHIEF ABRAMS TESTING SFAE GCSS W AB QT J MORAN 6501 ELEVEN MILE RD WARREN MI 48397-5000
1	COMMANDER WATERVLIET ARSENAL SMCWV QAE Q B VANINA BLDG 44 WATERVLIET NY 12189-4050
2	SFSJM CDL HQ US ARMY JNT MUNITIONS CMND AMSIO SMT R CRAWFORD W HARRIS 1 ROCK ISLAND ARSENAL ROCK ISLAND IL 61299-6000
2	COMMANDER US ARMY AMCOM AVIATION APPLIED TECH DIR J SCHUCK FORT EUSTIS VA 23604-5577
1	NSWC DAHLGREN DIV CODE G06 DAHLGREN VA 22448
2	US ARMY CORPS OF ENGR CERD C T LIU CEW ET T TAN 20 MASSACHUSETTS AVE NW WASHINGTON DC 20314
1	US ARMY TARDEC AMSRD TAR R D TEMPLETON 6501 E 11 MILE RD MS 263 WARREN MI 48397-5000

NO. OF  
COPIES ORGANIZATION

3 USA SBCCOM  
MATERIAL SCIENCE TEAM  
AMSSB RSS  
J HERBERT  
M SENNETT  
L-A BARKHOUSE  
KANSAS ST  
NATICK MA 01760-5057

2 COMMANDER  
US ARMY RDECOM  
AMSTA TR R  
J BENNETT  
D HANSEN  
MS 271  
WARREN MI 48397-5000

1 COMMANDER  
US ARMY RDECOM  
AMSTA TR D  
D OSTBERG  
MS 263  
WARREN MI 48397-5000

1 USA SBCCOM PM SOLDIER SPT  
AMSSB PM RSS A  
J CONNORS  
KANSAS ST  
NATICK MA 01760-5057

7 BENET LABS  
AMSTA AR CCB  
R FISCELLA  
G SPENCER  
R HASENBEIN  
AMSTA CCB R  
S SOPOK  
E HYLAND  
D CRAYON  
R DILLON  
WATERVLIET NY 12189-4050

1 NSWC  
TECH LIBRARY CODE B60  
17320 DAHLGREN RD  
DAHLGREN VA 22448

1 NSWC  
CRANE DIV  
M JOHNSON CODE 20H4  
LOUISVILLE KY 40214-5245

NO. OF  
COPIES ORGANIZATION

2 NSWC  
U SORATHIA  
C WILLIAMS CODE 6551  
9500 MACARTHUR BLVD  
WEST BETHESDA MD 20817

2 COMMANDER  
NSWC  
CARDEROCK DIV  
R PETERSON CODE 2020  
M CRITCHFIELD CODE 1730  
BETHESDA MD 20084

1 NAVAL SEA SYSTEMS CMND  
D LIESE  
1333 ISAAC HULL AVE SE 1100  
WASHINGTON DC 20376-1100

7 DIRECTOR  
US ARMY NGIC  
D LEITER MS 404  
M HOLTUS MS 301  
M WOLFE MS 307  
S MINGLEDORF MS 504  
J GASTON MS 301  
W GSTATTENBAUER MS 304  
J CRIDER MS 306  
2055 BOULDERS RD  
CHARLOTTESVILLE VA  
22911-8318

1 AFRL MLBC  
2941 P ST RM 136  
WRIGHT PATTERSON AFB OH  
45433-7750

1 DIRECTOR  
LOS ALAMOS NATL LAB  
F L ADDESSIO T 3 MS 5000  
PO BOX 1633  
LOS ALAMOS NM 87545

1 NSWC  
CARDEROCK DIV  
R CRANE CODE 6553  
9500 MACARTHUR BLVD  
WEST BETHESDA MD 20817-5700

1 AFRL MLMP  
R THOMSON  
2977 HOBSON WAY  
BLDG 653 RM 215  
WRIGHT PATTERSON AFB OH  
45433-7739

NO. OF  
COPIES ORGANIZATION

6 US ARMY RSRCH OFC  
H EVERITT  
J PRATER  
G ANDERSON  
D STEPP  
D KISEROW  
D SKATRUD  
PO BOX 12211  
RESEARCH TRIANGLE PARK NC  
27709-2211

7 US ARMY SBCCOM  
SOLDIER SYSTEMS CTR  
BALLISTICS TEAM  
J WARD  
W ZUKAS  
P CUNNIFF  
J SONG  
MARINE CORPS TEAM  
J MACKIEWICZ  
AMSSB RCP SS  
W NYKVIST  
S BEAUDOIN  
KANSAS ST  
NATICK MA 01760-5019

8 NSW  
J FRANCIS CODE G30  
D WILSON CODE G32  
R D COOPER CODE G32  
J FRAYSSE CODE G33  
E ROWE CODE G33  
T DURAN CODE G33  
L DE SIMONE CODE G33  
R HUBBARD CODE G33  
DAHLGREN VA 22448

2 AFRL MLMP  
F ABRAMS  
J BROWN  
2977 HOBSON WAY  
BLDG 653 RM 215  
WRIGHT PATTERSON AFB OH  
45433-7739

1 DIRECTOR  
LLNL  
STEVE DETERESA  
PO BOX 808  
LIVERMORE CA 94550

NO. OF  
COPIES ORGANIZATION

1 DIRECTOR  
LLNL  
L-125 FRANK MAGNESS  
PO BOX 808  
LIVERMORE CA 94550

1 DIRECTOR  
LLNL  
L-020 MILTON FINGER  
PO BOX 808  
LIVERMORE CA 94550

1 DIRECTOR  
LLNL  
L-099 MIKE MURPHY  
PO BOX 808  
LIVERMORE CA 94550

1 AFRL MLS OL  
L COULTER  
5851 F AVE  
BLDG 849 RM AD1A  
HILL AFB UT 84056-5713

1 OSD  
JOINT CCD TEST FORCE  
OSD JCCD  
R WILLIAMS  
3909 HALLS FERRY RD  
VICKSBURG MS 29180-6199

2 DARPA  
S WAX  
L CHRISTODOULOU  
3701 N FAIRFAX DR  
ARLINGTON VA 22203-1714

1 OAK RIDGE NATL LAB  
R M DAVIS  
PO BOX 2008  
OAK RIDGE TN 37831-6195

1 OAK RIDGE NATL LAB  
C EBERLE MS 8048  
PO BOX 2008  
OAK RIDGE TN 37831

3 NIST  
J CHIN MS 8621  
J MARTIN MS 8621  
D DUTHINH MS 8611  
100 BUREAU DR  
GAITHERSBURG MD 20899

NO. OF  
COPIES ORGANIZATION

1 OAK RIDGE NATL LAB  
C D WARREN MS 8039  
PO BOX 2008  
OAK RIDGE TN 37831

1 HYDROGEOLOGIC INC  
SERDP ESTCP SPT OFC  
S WALSH  
1155 HERNDON PKWY STE 900  
HERNDON VA 20170

3 DIRECTOR  
SANDIA NATL LABS  
APPLIED MECHS DEPT  
MS 9042  
J HANDROCK  
Y R KAN  
J LAUFFER  
PO BOX 969  
LIVERMORE CA 94551-0969

2 NASA LANGLEY RSRCH CTR  
AMSRD ARL VT  
F BARTLETT JR MS 266  
G FARLEY MS 266  
HAMPTON VA 23681-0001

1 FHWA  
E MUNLEY  
6300 GEORGETOWN PIKE  
MCLEAN VA 22101

1 USDOT FEDERAL RAILROAD  
M FATEH RDV 31  
WASHINGTON DC 20590

1 CYTEC FIBERITE  
R DUNNE  
1300 REVOLUTION ST  
HAVRE DE GRACE MD 21078

1 DIRECTOR  
NGIC  
IANG TMT  
2055 BOULDERS RD  
CHARLOTTESVILLE VA  
22911-8318

1 3TEX CORP  
A BOGDANOVICH  
109 MACKENAN DR  
CARY NC 27511

NO. OF  
COPIES ORGANIZATION

1 DIRECTOR  
DEFNS INTLLGNC AGCY  
TA 5  
K CRELLING  
WASHINGTON DC 20310

1 COMPOSITE MATERIALS INC  
D SHORTT  
19105 63 AVE NE  
PO BOX 25  
ARLINGTON WA 98223

1 JPS GLASS  
L CARTER  
PO BOX 260  
SLATER RD  
SLATER SC 29683

1 COMPOSITE MATERIALS INC  
R HOLLAND  
11 JEWEL CT  
ORINDA CA 94563

1 SIMULA  
R HUYETT  
10016 S 51ST ST  
PHOENIX AZ 85044

2 PROTECTION MATERIALS INC  
M MILLER  
F CRILLEY  
14000 NW 58 CT  
MIAMI LAKES FL 33014

1 ROM DEV CORP  
R O MEARA  
136 SWINEBURNE ROW  
BRICK MARKET PLACE  
NEWPORT RI 02840

1 TEXTRON SYSTEMS  
M TREASURE  
1449 MIDDLESEX ST  
LOWELL MA 01851

1 O GARA HESS & EISENHARDT  
M GILLESPIE  
9113 LESAINTE DR  
FAIRFIELD OH 45014

1 CONNEAUGHT INDUSTRIES INC  
J SANTOS  
PO BOX 1425  
COVENTRY RI 02816

NO. OF  
COPIES ORGANIZATION

1 ARMTEC DEFENSE PRODUCTS  
S DYER  
85 901 AVE 53  
PO BOX 848  
COACHELLA CA 92236

3 PACIFIC NORTHWEST LAB  
M SMITH  
G VAN ARSDALE  
R SHIPPELL  
PO BOX 999  
RICHLAND WA 99352

1 ALLIANT TECHSYSTEMS INC  
4700 NATHAN LN N  
PLYMOUTH MN 55442-2512

1 APPLIED COMPOSITES  
W GRISCH  
333 NORTH SIXTH ST  
ST CHARLES IL 60174

1 CUSTOM ANALYTICAL  
ENG SYS INC  
A ALEXANDER  
13000 TENSOR LANE NE  
FLINTSTONE MD 21530

1 AAI CORP  
DR N B MCNELLIS  
PO BOX 126  
HUNT VALLEY MD 21030-0126

1 PROJECTILE TECHLGY INC  
515 GILES ST  
HAVRE DE GRACE MD 21078

3 ALLIANT TECHSYSTEMS INC  
J CONDON  
E LYNAM  
J GERHARD  
WV01 16 STATE RT 956  
PO BOX 210  
ROCKET CENTER WV  
26726-0210

1 PRATT & WHITNEY  
C WATSON  
400 MAIN ST MS 114 37  
EAST HARTFORD CT 06108

NO. OF  
COPIES ORGANIZATION

3 NORTHROP GRUMMAN  
B IRWIN  
K EVANS  
D EWART  
BLDG 160 DEPT 3700  
1100 W HOLLYVALE ST  
AZUSA CA 91701

1 BRIGS COMPANY  
J BACKOFEN  
2668 PETERBOROUGH ST  
HERNDON VA 22071-2443

1 ZERNOW TECHL SERVICES  
L ZERNOW  
425 W BONITA AVE STE 208  
SAN DIMAS CA 91773

2 GENERAL DYNAMICS OTS  
FLINCHBAUGH DIV  
K LINDE  
T LYNCH  
PO BOX 127  
RED LION PA 17356

1 GKN WESTLAND AEROSPACE  
D OLDS  
450 MURDOCK AVE  
MERIDEN CT 06450-8324

1 AEROSPACE CORP  
G HAWKINS M4 945  
2350 E EL SEGUNDO BLVD  
EL SEGUNDO CA 90245

2 CYTEC FIBERITE  
M LIN  
W WEB  
1440 N KRAEMER BLVD  
ANAHEIM CA 92806

2 UDLP  
G THOMAS  
M MACLEAN  
PO BOX 58123  
SANTA CLARA CA 95052

NO. OF  
COPIES ORGANIZATION

5 SIKORSKY AIRCRAFT  
G JACARUSO  
T CARSTENSAN  
B KAY  
S GARBO MS S330A  
J ADELMANN  
6900 MAIN ST  
PO BOX 9729  
STRATFORD CT 06497-9729

2 UDLP  
R BRYNSVOLD  
P JANKE MS 170  
4800 E RIVER RD  
MINNEAPOLIS MN 55421-1498

1 LOCKHEED MARTIN  
SKUNK WORKS  
D FORTNEY  
1011 LOCKHEED WAY  
PALMDALE CA 93599-2502

1 NORTHRUP GRUMMAN CORP  
ELECTRONIC SENSORS  
& SYSTEMS DIV  
E SCHOCH MS V 16  
1745A W NURSERY RD  
LINTHICUM MD 21090

1 GDLS DIV  
D BARTLE  
PO BOX 1901  
WARREN MI 48090

1 GDLS  
M PASIK  
PO BOX 2074  
WARREN MI 48090-2074

1 GDLS  
MUSKEGON OPER  
M SOIMAR  
76 GETTY ST  
MUSKEGON MI 49442

1 GENERAL DYNAMICS  
AMPHIBIOUS SYS  
SURVIVABILITY LEAD  
G WALKER  
991 ANNAPOLIS WAY  
WOODBIDGE VA 22191

NO. OF  
COPIES ORGANIZATION

5 INST FOR ADVANCED  
TECH  
H FAIR  
I MCNAB  
P SULLIVAN  
S BLESS  
C PERSAD  
3925 W BRAKER LN  
AUSTIN TX 78759-5316

1 ARROW TECH ASSOC  
1233 SHELBURNE RD STE D8  
SOUTH BURLINGTON VT  
05403-7700

1 SAIC  
G CHRYSSOMALLIS  
8500 NORMANDALE LAKE BLVD  
STE 1610  
BLOOMINGTON MN 55437-3828

1 UCLA MANE DEPT ENGR IV  
H T HAHN  
LOS ANGELES CA 90024-1597

1 UMASS LOWELL  
PLASTICS DEPT  
N SCHOTT  
1 UNIVERSITY AVE  
LOWELL MA 01854

1 IIT RSRCH CTR  
D ROSE  
201 MILL ST  
ROME NY 13440-6916

1 MICHIGAN STATE UNIV  
MSM DEPT  
R AVERILL  
3515 EB  
EAST LANSING MI 48824-1226

1 PENN STATE UNIV  
R S ENGEL  
245 HAMMOND BLDG  
UNIVERSITY PARK PA 16801

1 PENN STATE UNIV  
C BAKIS  
212 EARTH ENGR  
SCIENCES BLDG  
UNIVERSITY PARK PA 16802

NO. OF  
COPIES ORGANIZATION

1 PURDUE UNIV  
SCHOOL OF AERO & ASTRO  
C T SUN  
W LAFAYETTE IN 47907-1282

1 UNIV OF MAINE  
ADV STR & COMP LAB  
R LOPEZ ANIDO  
5793 AEWB BLDG  
ORONO ME 04469-5793

1 JOHNS HOPKINS UNIV  
APPLIED PHYSICS LAB  
P WIENHOLD  
11100 JOHNS HOPKINS RD  
LAUREL MD 20723-6099

1 UNIV OF DAYTON  
J M WHITNEY  
COLLEGE PARK AVE  
DAYTON OH 45469-0240

2 UNIV OF DELAWARE  
CTR FOR COMPOSITE MTRLs  
J GILLESPIE  
S ADVANI  
201 SPENCER LAB  
NEWARK DE 19716

1 MISSISSIPPI STATE UNIV  
DEPT OF AEROSPACE ENGRG  
A J VIZZINI  
MISSISSIPPI STATE MS 39762

1 SOUTHWEST RSRCH INST  
ENGR & MATL SCIENCES DIV  
J RIEGEL  
6220 CULEBRA RD  
PO DRAWER 28510  
SAN ANTONIO TX 78228-0510

1 DREXEL UNIV  
A S D WANG  
3141 CHESTNUT ST  
PHILADELPHIA PA 19104

1 DEPT OF MTRLs  
SCIENCE & ENGRG  
UNIV OF ILLINOIS  
AT URBANA CHAMPAIGN  
J ECONOMY  
1304 W GREEN ST 115B  
URBANA IL 61801

NO. OF  
COPIES ORGANIZATION

3 UNIV OF TEXAS AT AUSTIN  
CTR FOR ELECTROMECHANICS  
J PRICE  
A WALLS  
J KITZMILLER  
10100 BURNET RD  
AUSTIN TX 78758-4497

3 DIRECTOR  
US ARMY RSRCH LAB  
AMSRD ARL WM MB  
A FRYDMAN  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1 DEPARTMENT HEAD  
US MILITARY ACADEMY  
K NYGREN  
CIVIL & MECH ENGRG DEPT  
WEST POINT NY 10996-1792

1 DIRECTOR  
US MILITARY ACADEMY  
D BOETTNER  
MECH ENGRG DIV  
WEST POINT NY 10996-1792

1 US ARMY ARDEC  
AMSRD AAR ATD  
B MACHAK  
BLDG 1  
PICATINNY ARSENAL NJ  
07806-5000

1 US ARMY ARDEC  
AMSRD AAR AEP E  
D CARLUCCI  
BLDG 94  
PICATINNY ARSENAL NJ  
07806-5000

10 HAWAII CORROSION LAB  
2540 DOLE ST  
HOMES HALL RM 302  
G HAWTHORN  
L HIHARA  
HONOLULU HI 96822

NO. OF  
COPIES ORGANIZATION

2 NORTH DAKOTA STATE UNIV  
DEPT OF COATINGS & POLYMERIC  
MTRLs  
G P BIERWAGEN  
V J GELLING  
1222 9TH ST S  
FARGO ND 58105-5516

2 OHIO STATE UNIV  
DEPT OF MTRLs SCIENCE & ENGRG  
G S FRANKEL  
R BUCHEIT  
2041 COLLEGE RD WATTS HALL  
COLUMBUS OH 43210-1179

1 UNIV OF CALIFORNIA BERKELEY  
COLLEGE OF ENGRG  
F M DOYLE  
308 MCLAUGHLIN HALL NO 1702  
BERKELEY CA 94720-1700

1 RENSSELEAR POLYTECHNIC INST  
DEPT OF MTRLs ENGRG  
D J DUQUETTE  
TROY NY 12818

1 THE BOEING COMPANY  
DIRECTOR OF MATRLs & PROCESS  
TECHLGY  
D CHONG  
2553 134TH AVE SE  
BELLEVUE WA 98005

1 UNIV OF VIRGINIA  
CTR FOR ELECTROCHEMICAL  
SCIENCE & ENGRG  
DEPT OF MTRLs SCIENCE & ENGRG  
J R SCULLY  
PO BOX 400745  
116 ENGRGS WAY  
CHARLOTTESVILLE VA 22904-4745

1 UNIV OF MICHIGAN  
DEPT OF MTRLs SCIENCE & ENGRG  
G S WAS  
H H DOW BLDG  
2300 HAYWARD ST  
ANN ARBOR MI 48109-2136

1 PENNSYLVANIA STATE UNIV  
B SHAW  
212 EES BLDG  
UNIV PARK PA 16870

NO. OF  
COPIES ORGANIZATION

1 EXPONENT INC  
MECHS & MTRLs DEPT  
R M LATANISION  
21 STRATHMORE RD  
NATICK MA 01760

1 NATIONAL MATERIALS ADVISORY  
BOARD  
M H MOLONEY  
500 FIFTH ST NW  
MS WS938  
WASHINGTON DC 20001

1 USMC  
MAINTENANCE CTR ALBANY  
S ALLEN  
28008 NEWCOMB RD  
ALBANY GA 31705

2 AIR FORCE CORROSION  
PREVENTION & CNTRL OFC  
K ANDREWS  
MAJ R REED  
325 RICHARD RAY BLVD BLDG 165  
ROBINS AFB GA 31098-1639

3 US ARMY TACOM TARDEC RDECOM  
AMSTA TR E1 MEPS 1267  
I C HANDSY  
J KOVANDA  
A BAZIARI  
6501 E 11 MILE RD BLDG 200A  
WARREN MI 48397-7738

5 US ARMY RDECOM  
AMSRD AMR PS AM  
S F CARR  
R A HERRON  
K BHANSALI  
M KANE  
A P STEELE  
BLDG 7103  
REDSTONE ARSENAL AL 35898

1 NASA CORROSION TECHLGY  
J CURRAN  
MS ASRC 20  
KENNEDY SPACE CENTER FL 32899



NO. OF  
COPIES ORGANIZATION

1 OUSD (A T & L)  
OFC OF CORROSION POLICY &  
OVERSIGHT  
D J DUNMIRE  
2001 N BEAUREGARD ST STE 210  
ALEXANDRIA VA 22311

1 OUSD FOR SCIENCE AND TECHLGY  
ODDR&E(S &T)  
MATRLS & STRUCTURES OFC  
L E SLOTER  
1777 N KENT ST STE 9030  
ARLINGTON VA 22209-2110

3 CONCURRENT TECHNOLOGIES CORP  
L GINTERT  
R MASON  
M SINGLETON  
7935 114 TH AVE  
LARGO FL 33773

3 US ARMY ERDC  
CONSTRUCTION ENGRG RSRCH LAB  
V HOCK  
A KUMAR  
L D STEPHENSON  
PO BOX 9005  
CHAMPAIGN IL 61826-9005

6 US ARMY ARDEC  
ARMY CORROSION OFC  
AMSRD AAR AEE P  
R ZANOWICZ  
J P THEIS  
D SKELTON  
D SCHMIDT  
J ZUNINO  
E MCCARTHY  
BLDG 60  
PICATINNY ARSENAL NJ 07806-5000

1 COMMANDER  
NAVSEAAIR  
CORROSION RSRCH & ENGRG BR  
R HAYS  
NSWCCD CODE 613  
9500 MACARTHUR BLVD  
WEST BETHESDA MD 20817-5700

NO. OF  
COPIES ORGANIZATION

2 COMMANDER  
NAVAIR  
MTRLs COATINGS & CORROSION  
C MATZDORF  
S SPADAFORA  
AIR 4 3 4 BLDG 2188  
PATUXENT RIVER MD 20670

2 BATTELLE MEMORIAL INST  
NATIONAL SECURITY DIV  
MATERIALS AND ENGRG GROUP  
W ABBOTT  
B HINDIN  
505 KING AVE  
COLUMBUS OH 43201-2693

ABERDEEN PROVING GROUND

1 US ARMY ATC  
CSTE DTC AT AD I  
W C FRAZER  
400 COLLERAN RD  
APG MD 21005-5059

102 DIR USARL  
AMSRD ARL CI  
AMSRD ARL O AP EG FI  
M ADAMSON  
AMSRD ARL WM  
J SMITH  
AMSRD ARL WM B  
CHIEF  
M ZOLTOSKI  
AMSRD ARL WM BA  
T KOGLER  
D LYON  
AMSRD ARL WM BC  
J NEWILL  
P PLOSTINS  
AMSRD ARL WM BD  
P CONROY  
B FORCH  
M LEADORE  
C LEVERITT  
R LIEB  
R PESCE-RODRIGUEZ  
B RICE  
A ZIELINSKI  
AMSRD ARL WM BF  
S WILKERSON  
AMSRD ARL WM M  
J MCCAULEY  
S MCKNIGHT  
J BEATTY

NO. OF COPIES	ORGANIZATION
	AMSRD ARL WM MA
	M VANLANDINGHAM
	L GHIORSE
	AMSRD ARL WM MB
	J BENDER
	T BOGETTI
	J BROWN
	L BURTON
	K CHO
	W DRYSDALE
	R EMERSON
	D GRAY
	D HOPKINS
	R KASTE
	L KECSKES
	H MAUPIN
	B POWERS
	D SNOHA (10 CPS)
	J SOUTH
	M STAKER
	J SWAB
	J TZENG
	AMSRD ARL WM MC
	R ADLER (10 CPS)
	K CHESONIS
	J ESCARSEGA
	B HART
	T JESSEN
	J KELLEY
	M MAHER
	C M MILLER
	F PIERCE
	B PLACZANKIS
	P SMITH
	W SPURGEON
	S K YOUNG
	AMSRD ARL WM MD
	B CHEESEMAN
	E CHIN
	P DEHMER
	R DOOLEY
	G GAZONAS
	S GHIORSE
	J LASALVIA
	J MONTGOMERY
	J SANDS
	D SPAGNUOLO
	S WALSH
	AMSRD ARL WM RP
	J BORNSTEIN
	E RIGAS
	C SHOEMAKER
	AMSRD ARL WM SG
	R CARTER

NO. OF COPIES	ORGANIZATION
	AMSRD ARL WM T
	P BAKER
	AMSRD ARL WM TA
	W BRUCHEY
	M BURKINS
	B GOOCH
	T HAVEL
	C HOPPEL
	E HORWATH
	J RUNYEON
	S SCHOENFELD
	AMSRD ARL WM TC
	R COATES
	AMSRD ARL WM TD
	D DANDEKAR
	M RAFTENBERG
	T WEERASOORIYA
	AMSRD ARL WM TE
	CHIEF
	J POWELL

NO. OF  
COPIES ORGANIZATION

1 ROYAL INSTITUTE OF TECHNOLOGY  
C LEYGRAF  
KTH DROTTNING VAG 51  
SE 100 STOCKHOLM SWEDEN

INTENTIONALLY LEFT BLANK.